

Kent Academic Repository

Full text document (pdf)

Citation for published version

Bebber, Michelle and Key, Alastair J. M. and Fisch, Michael and Meindle, Richard and Eren, Metin I. (2019) The exceptional abandonment of metal tools by North American hunter-gatherers, 3000 B.P. Scientific Reports, 9 . ISSN 2045-2322.

DOI

<https://doi.org/10.1038/s41598-019-42185-y>

Link to record in KAR

<https://kar.kent.ac.uk/73413/>

Document Version

Publisher pdf

Copyright & reuse

Content in the Kent Academic Repository is made available for research purposes. Unless otherwise stated all content is protected by copyright and in the absence of an open licence (eg Creative Commons), permissions for further reuse of content should be sought from the publisher, author or other copyright holder.

Versions of research

The version in the Kent Academic Repository may differ from the final published version.

Users are advised to check <http://kar.kent.ac.uk> for the status of the paper. **Users should always cite the published version of record.**

Enquiries

For any further enquiries regarding the licence status of this document, please contact:

researchsupport@kent.ac.uk

If you believe this document infringes copyright then please contact the KAR admin team with the take-down information provided at <http://kar.kent.ac.uk/contact.html>

SCIENTIFIC REPORTS



OPEN

The exceptional abandonment of metal tools by North American hunter-gatherers, 3000 B.P.

Michelle R. Bebber¹, Alastair J. M. Key², Michael Fisch³, Richard S. Meindl¹ & Metin I. Eren^{1,4}

Most prehistoric societies that experimented with copper as a tool raw material eventually abandoned stone as their primary medium for tool making. However, after thousands of years of experimentation with this metal, North American hunter-gatherers abandoned it and returned to the exclusive use of stone. **Why? We experimentally confirmed that replica copper tools are inferior to stone ones when each is sourced in the same manner as their archaeological counterparts and subjected to identical tasks. Why, then, did copper consistently lead to more advanced metallurgy in most other areas of the world? We suggest that it was the unusual level of purity in the North American copper sourced by North American groups, and that naturally occurring alloys yielded sufficiently superior tools to encourage entry into the copper-bronze-iron continuum of tool manufacture in other parts of the world.**

Metallurgy in North America may have begun as early as 7,000 years ago^{1,2}. By the Middle and Late Archaic periods between 6000 and 3000 B.P. a florescence of copper working, known as the Old Copper Culture, thrived in and around the world's largest naturally occurring pure copper deposit which is in North America's Lake Superior region³. During these millennia, hunter-gatherers stretching from central Canada to the eastern Great Lakes regularly made utilitarian implements out of copper^{4–12}, only for these items to decline in prominence and frequency as populations grew and social complexity increased during the Archaic to Woodland Transition^{1,13–17}. After 3000 B.P. prehistoric people in Eastern North America continued to use copper, but it was mostly relegated toward ritualized items^{16,18}.

Binford¹⁹ referred to this decline in utilitarian tools made from copper as the Old Copper Culture “technomic devolution”, and it is a unique event in archaeologists’ global understanding of prehistoric metallurgic evolution²⁰. While the use of stone implements often continued into the metal ages²¹, analogous ones produced from metal ultimately replaced these implements. Indeed, the near-global transition from stone to metal tools during the early- and mid-Holocene appears to be a ubiquitous, unidirectional transition^{22–26}. Cases where metal tools were indigenously innovated and used, but did not ultimately predominate or replace stone tools, are rare. Thus, the abandonment of Old Copper Culture utilitarian tools facilitates the examination of an exceptional situation in human prehistory: how and why metal tools were selected *against*.

Binford¹⁹ found this situation particularly “interesting” because of the general assumption that in terms of “absolute efficiency” copper tools were superior to their functional equivalents in stone, possessing both greater durability as well as superiority in accomplishing cutting and piercing tasks. However, acknowledging that the manufacture of copper tools would have required greater energy expenditure than stone tools, Binford¹⁹ maintained that copper tools would have still been more efficient in terms of net energy expenditure. This is because copper tools were “probably more durable and could have been utilized for a longer period of time”¹⁹. Thus, despite the greater energy required to produce a copper tool relative to a stone one, a copper tool’s durability would have conserved energy in task performance. Binford¹⁹ was less certain whether copper tools were superior to stone ones in cutting and piercing functions, suggesting that “only experiments can determine”¹⁹ that difference.

Current archaeological evidence is consistent with the hypothesis that population growth and increased social complexity contributed to the selection against utilitarian copper tools around 3000 B.P. Larger, more numerous, and more ostentatious cemeteries during the Late Archaic suggest that populations in the Upper Lakes were growing, and societies were becoming less egalitarian. One clear archaeological signal of increased burial

¹Department of Anthropology, Kent State University, Kent, OH, 44242, USA. ²School of Anthropology and Conservation, University of Kent, Canterbury, CT2 7NZ, UK. ³College of Aeronautics and Engineering, Kent State University, Kent, OH, 44242, USA. ⁴Department of Archaeology, Cleveland Museum of Natural History, Cleveland, OH, 44106, USA. Correspondence and requests for materials should be addressed to M.R.B. (email: mbebber@kent.edu)

ostentation is the interment of ornamental copper artifacts^{13,15,19}. Thus, it has been argued that an increasingly socially complex world required an increase in ornamental copper production, resulting in a concomitant production decline in utilitarian copper tools^{14–18,27}.

However, whether demographic and social factors *alone* led to the decline of utilitarian copper tools after 3000 B.P. is currently unknown because experimental tests examining Binford's¹⁹ assumptions regarding copper versus stone tool durability and cutting ability have yet to be conducted. Here, we assess those assumptions with replicas of the implement best suited to test both of these factors simultaneously: knives. We use a mechanical engineering approach that measures the amount of energy expenditure needed to complete a simple task—cutting a uniform substrate—to evaluate whether or not there exist differences in durability and cutting ability between knives made from copper versus those made from stone.

Materials and Methods

Thirty replica copper blades were produced by M.R.B.²⁰. The specimens were suitable in shape for controlled materials testing, but similar in composition and internal structure to those produced during the Late Archaic²⁰ (SI Appendix). The copper used for production of the experimental specimens was procured from same mining area that would have been used in ancient times, the Keweenaw Peninsula, Michigan^{1,2,28}. Thirty stone flakes were produced by A.J.M.K. and M.I.E. from Keokuk chert, a common toolstone used throughout the North American Midwest. Each edge angle of a copper blade specimen corresponded to a similar edge angle of a stone flake specimen (SI Appendix).

Our sharpness and durability cutting experiments follow closely the procedures described in Key *et al.*²⁹ (SI Appendix). We used an Instron Universal Materials Tester (Model 5967) in which peak force (N) and total work (J) during cutting were calculated for all specimens. Following Schuldt *et al.*³⁰, force and work are used as proxies for edge sharpness. In lieu of biological tissues, modern mechanical tests of sharpness regularly employ flexible soft solid plastics as the cutting substrate^{31–33}. This is due to the structural inconsistencies that exist in the muscle fibers of meat, which ultimately cause variation in the force and energy measurements. Here we use standard PVC (polyvinyl chloride) tubing with 6 mm O.D. cut to length of approximately 15 cm for mounting in the substrate grips.

We conducted three analyses comparing copper versus stone knives: initial sharpness, final sharpness, and durability. To assess initial sharpness, we measured the force and work necessary for the first cut of the substrate before the knives were blunted. To assess final sharpness, we averaged the force and work necessary to cut the substrate for each of the five subsequent cutting tests performed after a blunting event (SI Appendix). The lower force³⁰ and work required for a cut indicated a sharper tool. To assess durability³⁴ (in this case the ability of an edge to resist blunting over time), we used repeated test cuts with the same blade³⁵ to examine how much more force and work was required to cut the substrate for the post-blunting cutting events versus the initial cut. A smaller difference between these two values indicated a more durable material.

The sharpness and durability data were analyzed using IBM SPSS version 23. The nonparametric Mann-Whitney *U* tests with Monte Carlo permutation (10,000 permutations) and 95% confidence intervals were used for the analyses. Mann-Whitney *U* is a conservative statistical procedure that requires only minimal assumptions of the data^{36,37}. Effect size *r* was also calculated^{37,38}. All raw data can be found in Dataset S1.

Results

Initial sharpness. The results show stone knives are sharper than copper ones. The results for force ($U = 312.00$, $p = 0.041$, $r = 0.26$) show that the copper blades ($\bar{x} = 237.90$ N) required significantly more force to initiate and complete a cut than did the stone blades ($\bar{x} = 193.59$ N) (Fig. 1). Likewise, the results for work ($U = 257.00$, $p = 0.004$, $r = 0.37$) were highly significant and demonstrate that copper blades ($\bar{x} = 5.424$ J) require much more energy expenditure than do stone blades ($\bar{x} = 2.939$ J) to complete the initial cut (Fig. 1).

Final sharpness. The results show no difference between stone (force: $\bar{x} = 334.39$ N; work: 9.099 J) and copper (force: $\bar{x} = 347.55$ N; work: 10.101 J) knives after each was blunted (Fig. 1). There was no significant difference between the two groups either in the amount of force ($U = 426.00$, $p = 0.723$) and the amount of work ($U = 429.50$, $p = 0.762$) needed to cut the substrate.

Durability. Copper knives were more durable than the stone knives (Fig. 1). The copper knives showed an increase between initial and final sharpness of 109.65 N and 4.677 J, while the stone knives showed an increase between initial and final sharpness of 140.04 N and 6.16 J. The copper blades' increase in force and work required to cut the substrate was significantly less than that of the stone knives (force: $U = 296.00$, $p = 0.023$, $r = 0.29$; work: $U = 302.00$, $p = 0.029$, $r = 0.28$).

Discussion

The selection against metal in the evolution of human technology is a rare occurrence. Why would people select against what is widely perceived to be a 'superior' raw material – metal – and revert back to a seemingly 'inferior' one – stone? Yet, by 3000 B.P., Late Archaic foraging societies of the North American Upper Great Lakes transitioned away from the utilitarian copper tools they had been using for millennia^{1,13–17}. While demographic and social factors likely played a role in this event^{13–15,17,19,27}, the role of copper versus stone durability and sharpness has not previously been investigated – despite Binford's¹⁹ now 50-year-old discussion and explicit calls for experimentation.

Our results demonstrated that North American copper knives are more durable than analogous ones made from stone, supporting Binford's¹⁹ assumption. But stone knives are initially sharper, and after an equal number of blunting events, copper and stone knives possess the same sharpness. Thus, copper knives' greater durability does not actually provide any advantage in terms of functional efficiency. A tool-user might as well receive the

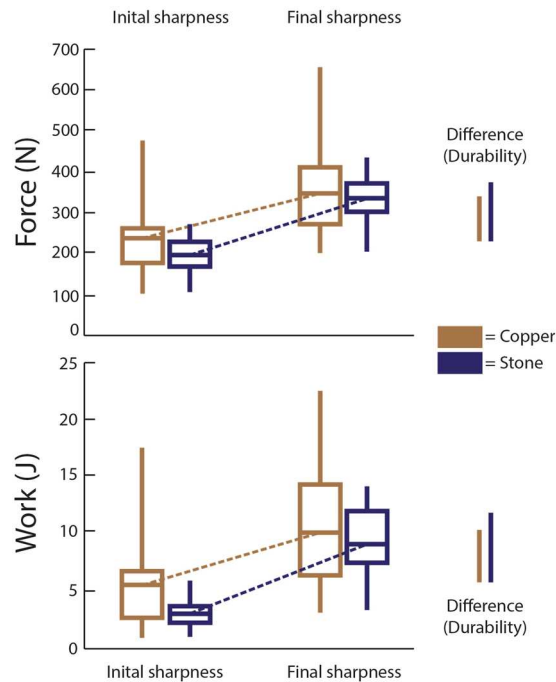


Figure 1. The force (N) and work (J) necessary for copper (brown) and stone (dark blue) blades to cut through a substrate. Stone blades are significantly sharper than copper ones initially, and after blunting there is no difference. Copper is more durable given it loses less sharpness.

front-loaded advantage of stone knives' initial sharpness knowing that the greater rate of stone sharpness loss over several blunting events will ultimately result in a stone knife of the same functional efficiency as a copper knife having undergone the same amount of blunting. It is important to emphasize that these results do not consider the energy required to produce copper or stone tools, with copper requiring substantially more¹⁹, further increasing the efficiency advantages of stone. Overall, these results are consistent with the hypothesis that the selection against metal utilitarian tools by North American Late Archaic foragers required multiple contributing factors: demography, social reasons, *and* functional efficiency. Unless all of these factors act in concordance, humans will select metals over stone – which is what we typically see in the global archaeological record – and metal tools will eventually predominate over, or entirely replace, stone ones. In other words, the Old Copper Culture technomic devolution was likely an accident of history.

Two broad questions warrant further consideration. First, was functional efficiency a predominate or minor contributor to the Old Copper Culture technomic devolution, and was this contribution in terms of absolute efficiency, that is functional efficiency independent of production costs, or in terms of overall net energy expenditure? Second, what is the comparative functional efficiency of stone and metal utilitarian implements in prehistoric contexts where metal predominates or replaces stone? To better understand these questions, a comprehensive, experimental program is needed that engages with a variety of analogous tool types made from both copper and stone, which records the energetics of producing each, and assesses efficiency while using them. Additionally, with respect to the second question, light will be thrown on the differential evolutionary success of metal technology in different parts of the prehistoric world via direct comparisons between New World and Old World copper in terms of their elemental and geochemical composition, methods of production, and resulting materials properties.

References

- Martin, S. *Wonderful Power: the Story of Ancient Copper Working in the Lake Superior Basin*. (Wayne State University Press, Detroit, 1999).
- Trevelyan, A. *Miskwabik, Metal of Ritual: Metallurgy in Precontact Eastern North America*. (University Press of Kentucky, Lexington, 2015).
- LaBerge, G. *Geology of the Lake Superior Region*. (Geoscience Press, Tucson, 1994).
- Gibbon, G. Old copper in Minnesota: a review. *Plains Anthropol* **43**, 27–50 (1998).
- Levine, M. Native copper in the Northeast: An overview of potential sources available to indigenous peoples. The Archaeological Northeast, eds Levine, M., Sassaman, K. & Nassaney, M. (Bergin and Garvey, Westport, CT), pp 183–199 (1999).
- Levine, M. Determining the provenance of native copper artifacts from northeastern North America: Evidence from instrumental neutron activation analysis. *J Archaeol Sci* **34**, 572–587 (2007a).
- Levine, M. Overcoming disciplinary solitude: the archaeology and geology of native copper in eastern North America. *Geoarchaeol* **22**, 49–66 (2007b).
- Mason, R. *Great Lakes Archaeology*. (Academic Press, New York, 1981).
- Steinbring, J. Old copper culture artifacts in Manitoba. *Am Antiq* **31**, 567–574 (1966).
- Wittry, W. A preliminary study of the old copper complex. *Wisconsin Archeol* **32**, 1–18 (1951).
- Wittry, W. & Ritzenthaler, R. The old copper complex: an Archaic manifestation in Wisconsin. *Am Antiq* **21**, 244–254 (1956).

12. Vernon, W. New archaeometallurgical perspectives on the old copper industry of North America. *Geological Society of America Centennial Special* **4**, 499–512 (1990).
13. Ehrhardt, K. Copper working technologies, contexts of use, and social complexity in the Eastern Woodlands of Native North America. *J World Prehistory* **22**, 213–235 (2009).
14. Martin, S. & Pleger, T. The complex formerly known as a culture: the taxonomic puzzle of old copper. *Taming the Taxonomy: Toward a New Understanding of Great Lakes Archaeology*, eds Williamson R, Watts C (Eastend Books, Toronto) pp 61–70 (1999).
15. Pleger, T. Old copper and red ochre social complexity. *Midcont J Archaeol* **25**, 169–190 (2000).
16. Pleger, T. A brief introduction to the old copper complex of the Western Great Lakes: 4000–1000 BC. In: *Proceedings of the Twenty-seventh Annual Meeting of the Forest History Association of Wisconsin, Inc*, pp. 10–18 (2002).
17. Pleger, T. & Stoltman, J. The Archaic Tradition in Wisconsin. *Archaic Societies: Diversity and Complexity across the Midcontinent*, eds Emerson, T., McElrath, D. & Fortier, A. (SUNY Press, Albany, NY), pp 697–724 (2009).
18. LaRonge, M. An experimental analysis of Great Lakes Archaic copper smelting. *N Am Archaeol* **22**, 371–385 (2001).
19. Binford, L. Archaeology as anthropology. *Am Antiq* **28**, 217–225 (1962).
20. Beber, M. & Eren, M. Toward a functional understanding of the North American Old Copper Culture “technomic devolution”. *J Archaeol Sci* **98**, 34–44 (2018).
21. Rosen, S. *Lithics after the Stone Age: a handbook of stone tools from the Levant* (Rowman Altamira, Lanham, 1997).
22. La Niece, S., Hook, D.-R. & Craddock, P.-T. eds *Metals and mines: Studies in archaeometallurgy*. (Archetype Publications, London, 2007).
23. Killick, D. & Fenn, T. Archaeometallurgy: the study of preindustrial mining and metallurgy. *Annual Review of Anthropology*, **41** (2012).
24. Mei, J. & Rehren, T. eds *Metallurgy and Civilisation: Eurasia and Beyond: Proceedings of the 6th International Conference on the Beginnings of the Use of Metals and Alloys BUMA VI*. (Archetype Publications, London, 2009).
25. Roberts, B.-W. & Thornton, C.-P. eds *Archaeometallurgy in global perspective: methods and syntheses*. (Springer Science & Business Media, Berlin, 2014).
26. Tylecote, R.-F. *A history of metallurgy*. (Institute of materials, London, 1992).
27. Pleger, T. *Social Complexity, Trade, and Subsistence during the Archaic/Woodland Transition in the Western Great Lakes (4000–400 B.C.): a Diachronic Study of Copper Using Cultures at the Oconto and Riverside Cemeteries*. Ph.D. dissertation. Department of Anthropology, University of Wisconsin-Madison. (University Microfilms International, Ann Arbor, Michigan, 1998).
28. Griffin, J. *Lake Superior copper and the Indians: miscellaneous studies of Great Lakes prehistory*. *Anthropological Papers, Museum of Anthropology*, vol. 17 (University of Michigan, Ann Arbor, 1961).
29. Key, A., Fisch, M. & Eren, M. Early stage blunting causes rapid reductions in stone tool performance. *J Archaeol Sci* **91**, 1–11 (2018).
30. Schuldt, S., Arnold, G., Kowalewski, J., Schneider, Y. & Rohm, H. Analysis of the sharpness of blades for food cutting. *Journal of Food Engineering* **188**, 13–20 (2016).
31. Marsot, J., Claudon, L. & Jacqmin, M. Assessment of knife sharpness by means of a cutting force measuring system. *Appl Ergon* **38**(1), 83–89 (2007).
32. McCarthy, C.-T., Hussey, M. & Gilchrist, M.-D. On the sharpness of straight edge blades in cutting soft solids: Part I—indentation experiments. *Eng Fract Mech* **74**(14), 2205–2224 (2007).
33. Schuldt, S., Arnold, G., Roschy, J., Schneider, Y. & Rohm, H. Defined abrasion procedures for cutting blades and comparative mechanical and geometrical wear characterization. *Wear* **300**(1–2), 38–43 (2013).
34. Cooper, T. The durability of consumer durables. *Business Strategy and the Environment* **3**(1), 23–30 (1994).
35. Atkins, T. *The science and engineering of cutting: the mechanics and processes of separating, scratching and puncturing biomaterials, metals and non-metals* (Butterworth-Heinemann, Oxford, 2009).
36. Dytham, C. *Choosing and using statistics: a biologist's guide*. (John Wiley & Sons, Hoboken, 2011).
37. Field, A. *Discovering statistics using IBM SPSS statistics* (Sage, Thousand Oaks, 2013).
38. Smith, R.-J. The continuing misuse of null hypothesis significance testing in biological anthropology. *Am J Phys Anthropol* **166**(1), 236–245 (2018).

Author Contributions

M.R.B. and M.I.E. conceived of the experiment and wrote manuscript text. M.R.B., M.F. and A.J.M.K. produced experimental specimens. M.F. advised data collection. M.R.B. and A.J.M.K. collected all data. R.S.M., M.R.B. and M.I.E. analyzed data. MRB and MIE prepared all figures. All authors edited the manuscript text.

Additional Information

Supplementary information accompanies this paper at <https://doi.org/10.1038/s41598-019-42185-y>.

Competing Interests: The authors declare no competing interests.

Publisher's note: Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.



Open Access This article is licensed under a Creative Commons Attribution 4.0 International License, which permits use, sharing, adaptation, distribution and reproduction in any medium or format, as long as you give appropriate credit to the original author(s) and the source, provide a link to the Creative Commons license, and indicate if changes were made. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in a credit line to the material. If material is not included in the article's Creative Commons license and your intended use is not permitted by statutory regulation or exceeds the permitted use, you will need to obtain permission directly from the copyright holder. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>.

© The Author(s) 2019