



# Kent Academic Repository

Xia, JiaChen, Guo, Jian, Zhang, Xi, Lan, Mu, Wen, Jiqui, Wang, Shanling, He, Yi, Xiang, Gang, Corrias, Anna and Boi, Filippo (2021) *Anomalous stepped-hysteresis and T-induced unit-cell-volume reduction in carbon nanotubes continuously filled with faceted Fe<sub>3</sub>C nanowires*. *Nano Express*, 2 (1).

## Downloaded from

<https://kar.kent.ac.uk/86638/> The University of Kent's Academic Repository KAR

## The version of record is available from

<https://doi.org/10.1088/2632-959X/abe605>

## This document version

Author's Accepted Manuscript

## DOI for this version

## Licence for this version

CC BY (Attribution)

## Additional information

## Versions of research works

### Versions of Record

If this version is the version of record, it is the same as the published version available on the publisher's web site. Cite as the published version.

### Author Accepted Manuscripts

If this document is identified as the Author Accepted Manuscript it is the version after peer review but before type setting, copy editing or publisher branding. Cite as Surname, Initial. (Year) 'Title of article'. To be published in *Title of Journal*, Volume and issue numbers [peer-reviewed accepted version]. Available at: DOI or URL (Accessed: date).

## Enquiries

If you have questions about this document contact [ResearchSupport@kent.ac.uk](mailto:ResearchSupport@kent.ac.uk). Please include the URL of the record in KAR. If you believe that your, or a third party's rights have been compromised through this document please see our [Take Down policy](https://www.kent.ac.uk/guides/kar-the-kent-academic-repository#policies) (available from <https://www.kent.ac.uk/guides/kar-the-kent-academic-repository#policies>).

ACCEPTED MANUSCRIPT • OPEN ACCESS

# Anomalous stepped-hysteresis and T-induced unit-cell-volume reduction in carbon nanotubes continuously filled with faceted Fe<sub>3</sub>C nanowires

To cite this article before publication: JiaChen Xia *et al* 2021 *Nano Ex.* in press <https://doi.org/10.1088/2632-959X/abe605>

## Manuscript version: Accepted Manuscript

Accepted Manuscript is “the version of the article accepted for publication including all changes made as a result of the peer review process, and which may also include the addition to the article by IOP Publishing of a header, an article ID, a cover sheet and/or an ‘Accepted Manuscript’ watermark, but excluding any other editing, typesetting or other changes made by IOP Publishing and/or its licensors”

This Accepted Manuscript is © 2021 The Author(s). Published by IOP Publishing Ltd.

As the Version of Record of this article is going to be / has been published on a gold open access basis under a CC BY 3.0 licence, this Accepted Manuscript is available for reuse under a CC BY 3.0 licence immediately.

Everyone is permitted to use all or part of the original content in this article, provided that they adhere to all the terms of the licence <https://creativecommons.org/licenses/by/3.0>

Although reasonable endeavours have been taken to obtain all necessary permissions from third parties to include their copyrighted content within this article, their full citation and copyright line may not be present in this Accepted Manuscript version. Before using any content from this article, please refer to the Version of Record on IOPscience once published for full citation and copyright details, as permissions may be required. All third party content is fully copyright protected and is not published on a gold open access basis under a CC BY licence, unless that is specifically stated in the figure caption in the Version of Record.

View the [article online](#) for updates and enhancements.

# Anomalous stepped-hysteresis and T-induced unit-cell-volume reduction in carbon nanotubes continuously filled with faceted Fe<sub>3</sub>C nanowires

JiaChen Xia<sup>1+</sup>, Jian Guo<sup>1,4+</sup>, Xi Zhang<sup>1,2</sup> Mu Lan<sup>1,2</sup>, Jiqui Wen<sup>3</sup>, Shanling Wang<sup>3</sup>, Yi He<sup>3</sup>, Gang Xiang<sup>1,2\*</sup>, Anna Corrias<sup>5\*</sup> and Filippo S.Boi<sup>1\*</sup>

+ these authors contributed equally to this work

1 College of Physics, Sichuan University, Chengdu, China

2 Key Laboratory of High Energy Density Physics and Technology of Ministry of Education, Sichuan University, Chengdu, China

3 Analytical & Testing Center, Sichuan University, Chengdu, China

4 Department of Chemistry, University College London, London, UK

5 School of Physical Sciences, University of Kent, Canterbury, UK

\*Corresponding authors email: f.boi@scu.edu.cn, a.corrias@kent.ac.uk, gxiang@scu.edu.cn

## Abstract

Ferromagnetically-filled carbon nanotubes have been recently considered important candidates for application into data recording quantum disk devices. Achievement of high filling rates of the ferromagnetic materials is particularly desirable for applications. Here we report the novel observation of carbon nanotubes continuously filled along the capillary with unusual  $\mu\text{m}$ -long faceted Fe<sub>3</sub>C nanowires. Anomalous magnetic features possibly due to strain effects of the crystal facets are reported. Magnetization measurements revealed unusual stepped magnetic hysteresis-loops at 300 K and at 2 K together with an anomalous decrease in the coercivity at low temperature. The observed unusual shape of the hysteresis is ascribed to the existence of an antiferromagnetic transition within or at the boundary of the ferromagnetic facets. The collapse in the coercivity value as the temperature decreases and the characteristic width-enhancement of the hysteresis with the field increasing appear to indicate the existence of layered antiferromagnetic phases, possibly in the strain-rich regions of the nanowire facets. Zero field cooled (ZFC) and field cooled (FC) magnetic curves evidenced presence of magnetic irreversibilities, an indicator of a possible spin-glass-like behavior induced by competing antiferromagnetic and ferromagnetic interactions. Characterization performed with low temperature XRD measurements, further revealed a slight variation in the average Fe<sub>3</sub>C unit cell parameters, suggesting the absence of additional unit-cell volume induced ferromagnetic transitions at low temperature.

## Introduction

Molecular clusters behaving as single molecular magnets are typically able to show quantum tunnelling of magnetization at low temperatures [1-9] due to a ground state with a giant spin and an easy-axis of magnetization. These properties are different with respect to those measured in typical nano-ferromagnetic systems [10-16] where, owing to a large number of spins ( $10^5$ - $10^8$ ), the observation of quantum tunnelling is not trivial [16-31]. Interestingly Wernsdorfer et al., showed that 5 types of stepped-hysteresis loops could be obtained in the case of ferromagnetic nanoparticles [16]. It was also shown that the magnetization reversal of a single ferromagnetic nanoparticle could be described by thermal activation over a single-energy barrier [17]. However, in agreement with the predicted cross-over temperature [18-19] ( $T = 20$  mK), no quantum effects were reported. Observation of staircase-like hysteresis loops has been reported also in diluted magnetic semiconductors, examples of these systems include (In, Mn)As at low temperatures. In these systems formation of multiple magnetization jumps have been generally attributed to the depinning processes of magnetic domain walls [36]. Also, the formation of unusual magnetization steps, so-called Barkhausen jumps, has been reported in the presence of structural defects which strongly affect the magnetization process [33-35]. These effects have been recently observed in the specific cases of iron carbide/iron interfaces [35] and polycrystalline  $\alpha$ -Fe-filled materials encapsulated within carbon nanotubes (CNTs) [33].

Possible influence of Kondo effects in such phenomena has been also excluded in recent Seebeck-studies [32].

Differently from these examples, other types of stepped hysteresis loops have been reported to arise in materials where coexistence of superparamagnetic- and ferromagnetic-single-domain- grains is present [37-40]. Existence of such magnetic phenomena has been also reported in conditions of: I) coexistence of two magnetic components with contrasting coercivities, II) relatively high ratios of the coercivity remanence to coercive force and III) low coercivity components as large fraction of the total volume of the magnetic grains [37-40].

1  
2  
3  
4 Additionally, the values of magnetic moment for certain types of ferromagnetic crystals  
5 (i.e. iron carbide  $\text{Fe}_3\text{C}$ ) have been reported to change under certain conditions of unit  
6 cell volume contraction [28, 41-44]. Interestingly, observation of temperature-driven  
7 structural transitions in CNTs filled with  $\text{Fe}_3\text{C}$  nano-crystals was reported in a recent  
8 work by Boi et al. [41]. In that study, temperature dependent X-ray diffraction (T-XRD)  
9 measurements from 12 K to 298 K and Rietveld refinement analyses revealed a  
10 cooperative reversible  $2\theta$ -shift in both the 002 peak of the graphitic CNTs-walls and  
11 the 031 and 131 peaks of the encapsulated  $\text{Fe}_3\text{C}$  nano-crystals, evidencing a contraction  
12 in the average unit-cell volume of  $\text{Fe}_3\text{C}$  with the decrease of the temperature [41].  
13 Unusual variation of the magnetization with temperature and applied field in CNTs  
14 films containing a large quantity of  $\text{Fe}_3\text{C}$  were also reported by Karmakar et al. by  
15 SQUID magnetometry [43] and attributed to exchange bias effects resulting from  
16 magnetic interaction with secondary  $\gamma$ -Fe -phases (inside the CNTs) [43].

17 Appearance of butterfly shaped signal in the magnetization hysteresis has been also  
18 indicated as a hint to ferrimagnetism (see Mihalik et and Wollan et al. in ferrimagnetic  
19 oxide-based materials ( $\text{NdMn}_{1-x}\text{FexO}_{3+\delta}$ ) and  $[(1-x)\text{La}, x\text{Ca}]\text{MnO}_3$  systems [45,46]).  
20 Unusual hysteresis shapes were reported also by Hellwig et al. in presence of an  
21 antiferromagnetic-coupling effect between ferromagnetic multilayers [48].

22 In this work we report the novel observation of anomalously stepped hysteresis loops  
23 exhibiting a temperature-induced collapse in the magnetic coercivity parameter, in  
24 multiwall carbon nanotubes (MWCNTs) filled with faceted long ferromagnetic  $\text{Fe}_3\text{C}$   
25 nanowires (diameter of 40-60 nm and length of 1-5 micrometres).

26 The encapsulated nanowires were found to exhibit a unit-cell with averagely large  
27 atomic-parameters  $a = 0.5109243$  nm,  $b = 0.6765692$  nm,  $c = 0.4543652$  nm and an  
28 average volume of  $0.15706$  nm<sup>3</sup>.

29 The observed magnetic phenomenon is ascribed to the possible existence of layered  
30 antiferromagnetic interactions at the defective grain boundaries of the  $\text{Fe}_3\text{C}$ -facets  
31 (created by the fast cooling) within the  $\mu\text{m}$ -long faceted nanowires. The change in the  
32 coercivity parameters with the decrease of the temperature from 300 K to 2K cannot be  
33 explained on the basis of previous works on Fe-filled nanotubes. The appearance of  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

1  
2  
3  
4 such strained faceted features (as revealed by high resolution transmission electron  
5 microscopy (HRTEM)) in the encapsulated nanowires and the observed Fe<sub>3</sub>C-unit cell  
6 reduction, as revealed by T- XRD and Rietveld refinements, implies instead the possible  
7 formation of ferromagnetic-antiferromagnetic interfaces at low temperature. Zero field  
8 cooled (ZFC) and field cooled (FC) magnetic curves highlighted the presence of  
9 magnetic irreversibilities, an indicator of a possible spin-glass-like behavior induced by  
10 competing antiferromagnetic and ferromagnetic interactions.

11  
12 The observed small variation in the average Fe<sub>3</sub>C unit cell parameters, as extracted by  
13 Rietveld refinements, further suggest the absence of unit-cell volume induced magnetic  
14 moment transitions [28].

## 23 Experimental

24  
25 MWCNTs filled with Fe<sub>3</sub>C nanowires (diameter of 40-60 nm) were produced by  
26 sublimation and pyrolysis of ferrocene and dichlorobenzene mixtures (40 mg of  
27 ferrocene were mixed with one drop of dichlorobenzene). A quartz tube reactor of 1.5  
28 m and an Ar flow rate of 11 ml/min were used. The samples were cooled down with  
29 cooling times of 10-20 min by removing the furnace along a rail system (quench).  
30 Different sublimation temperatures were used (the value of sublimation temperature  
31 was measured within the area occupied by the ferrocene-containing quartz boat, within  
32 the quartz tube reactor), and the pyrolysis temperature was 990 °C. The duration of each  
33 reaction was 10 minutes. Fe<sub>3</sub>C filled carbon nano-onions (CNOs) were produced for  
34 comparative purposes, following the method reported in ref.47. Different average unit-  
35 cell volumes (determined via Rietveld refinement of the XRD patterns) were obtained  
36 for the MWCNTs depending on the used sublimation temperature: 0.15528 nm<sup>3</sup> with  
37 630-700 °C; 0.15608 nm<sup>3</sup> with 530-600°C; 0.15706 nm<sup>3</sup> with 460-530 °C and 0.15778  
38 nm<sup>3</sup> with 360-460 °C. Note that the observed effect was then found to vanish for larger  
39 quantities of ferrocene (i.e. ~ 100- 200 mg), owing to the increase of the overall CNTs-  
40 diameter and systematic differences in the carbon to metal ratios within the pyrolyzed  
41 vapor. A 200 kV American FEI Tecnai G2F20 HRTEM and a Philips X'pert Pro MPD  
42 powder X-ray diffractometer (Cu K- $\alpha_{1,2}$ ,  $\lambda = 0.15418$  nm) were employed for the  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

crystal characterization. The magnetic characterization was performed at 300 K with a vibrating sample magnetometry 2.5 Tesla electromagnet East Changing 9060 by using a magnetic field of 13000 Oe and at 2 K with a Quantum Design Superconducting Quantum Interference Device by using the magnetic field of 10000 Oe. T-XRD measurements were performed on a PANalytical Empyrean powder X-ray diffractometer, equipped with a primary Johansson monochromator (Cu K- $\alpha_1$ ,  $\lambda = 0.15406$  nm), an Oxford Cryosystems PheniX cryostat operating under vacuum below  $10^{-2}$  Pa, and a X'celerator linear detector. Measurements were collected from 12 K to 298 K (12 K, 20 K, 30 K, 40 K, 50 K, 60 K, 70 K, 80 K, 90 K, 100 K, 120 K, 140 K, 160 K, 180 K, 200 K, 220 K, 240 K, 260 K, 280 K and 298 K). See also ref. [49] for comparative SQUID magnetometry measurements on Fe<sub>3</sub>C filled CNOs, in absence of nanowire facets.

## Results and Discussion

A typical example of MWCNTs completely filled with a Fe<sub>3</sub>C nanowire is shown in the transmission electron micrograph of Fig.1A. It is interesting to notice that a variation in the volume distribution of the Fe<sub>3</sub>C crystal along the MWCNT-core is present with the formation of unusually faceted atomic lattice periodicities characterized by repeated dark and bright contrasts within individual encapsulated nanowires. A typical XRD measurement confirming the presence of Fe<sub>3</sub>C in the sample is shown in Fig.2. The Fe<sub>3</sub>C phase was identified by the 210, 002, 201, 211, 102, 220, 031, 112, 131, 221 and 122 reflections. The unit cell parameters determined via Rietveld refinement were:  $a = 0.5109243$  nm,  $b = 0.6765692$  nm,  $c = 0.4543652$  nm (unit cell volume of  $0.15706$  nm<sup>3</sup>). Detailed HRTEM measurements revealed further a high detail of the Fe<sub>3</sub>C crystal-lattice. As shown in Fig.1B and Figs.3,4 slight variations in the lattice parameters could be probed in different regions of the encapsulated carbide nanowires. In the inset of Fig.1C, the reduced Fourier transform allowed to identify the 100 (cyan circles) and 001 (yellow circles) lattice planes of Fe<sub>3</sub>C with space group Pnma corresponding to the spacings of approximately 0.51 nm and 0.45 nm respectively.

Presence of unusual hysteresis loops, characterized by a characteristic width-

1  
2  
3  
4 enhancement with the field increasing was revealed in the room-temperature  
5 magnetization vs applied field hysteresis (see rose-colored hysteresis Fig. 5A and B) of  
6 a powdered-sample comprising many randomly oriented filled MWCNTs as those  
7 shown in Fig.1. Two steps were identified at approximately 492 Oe, 22.4 emu/g, and at  
8 -460 Oe, -22.9 emu/g. A saturation magnetization of 109 emu/g and a coercivity of 850  
9 Oe were measured.

10  
11 The hysteresis loop was further measured also at 2K (see Fig.5A and 5B, dark magenta  
12 hysteresis). These measurements revealed a temperature-induced shift in the step-  
13 position together with an increase in the length parameter of each step. The two  
14 anomalously long step-features were found at 96.6 Oe, 37 emu/g and at -100 Oe, -37  
15 emu/g. The length of each step was found to be 58-62 emu/g. An extremely low  
16 coercivity of 100 Oe and a higher saturation magnetization of 120 emu/g were also  
17 measured at low temperature. We can immediately notice that these properties are  
18 very different with respect to those reported at 0.2 K by Wernsdorfer et al. [16]. Also,  
19 the observed trend is significantly different with respect to that measured by Boi et al.  
20 in non-faceted Fe<sub>3</sub>C filled CNOs in ref.49, where a progressive increase in the  
21 coercivity parameter with the decrease of the temperature was found.

22  
23 Stepped hysteresis loops have been reported also in the case of single-molecule magnets  
24 [1,9], nanomagnets [25-26], FeC crystals and Fe/Sm multilayers [20-27]. However due  
25 to the large number of atomic periodicities comprised in the Fe<sub>3</sub>C nanowires, the  
26 temperature of observation and the unusual dynamics of coercivity decrease, the origin  
27 of the observed step features is not attributable to quantum tunnelling of magnetization  
28 effects or the possible presence of a wasp-waisted hysteresis loops. Instead, given the  
29 presence of strained regions in the encapsulated nanowires, the formation of  
30 ferromagnetic/antiferromagnetic interfacial features is possible [48]. Comparing the  
31 observed hysteresis in Fig.5B with those observed in antiferromagnetically-coupled  
32 ferromagnetic multilayers, a similarity in the shape of the hysteresis is noticeable [48].  
33 Additional investigation of this magnetic transition was considered by employing ZFC  
34 and FC methods to extract the variation of the magnetic moment with temperature.

35  
36 Fig.6 shows the ZFC and FC magnetization vs temperature signals acquired from 2K  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

1  
2  
3  
4 to 300K at the field of 300 Oe. It is important to notice the existence of a spin-glass-  
5 like behavior in both the analyzed portions of the filled CNTs in Fig.6A-B, which may  
6 be an indicator of competing ferromagnetic and antiferromagnetic ordering within the  
7 same sample [50-51].  
8  
9

10  
11 Further investigation of the possible existence of T-induced structural variation in the  
12  $\text{Fe}_3\text{C}$  unit-cell volume was considered by employing T-XRD and Rietveld refinements.  
13 These Rietveld refinements were performed on the same dataset acquired in ref.41 for  
14 CNTs filled partially/or continuously with  $\text{Fe}_3\text{C}$ . Repeated Rietveld refinements were  
15 performed on a narrower  $2\theta$  region (from  $39^\circ$  to  $50^\circ$   $2\theta$ ) of the XRD patterns with  
16 respect to the refinements reported in reference [41], allowing for a more accurate  
17 estimation of the unit-cell volume parameters.  
18  
19

20  
21 Plots showing the variation of the 100, 010 and 001  $\text{Fe}_3\text{C}$  axis values are shown in  
22 Fig.7A-H (on CNTs partially and continuously filled with  $\text{Fe}_3\text{C}$ ), and plots showing the  
23 unit-cell volume parameters are shown in Figs.7D,H (see typical examples in ESI Fig.1  
24 and ESI Fig.2). Note that this more accurate estimation of the unit-cell volume indicates  
25 a contraction of 0.52% in the continuously filled CNTs case (Fig.7D) and of 0.06% in  
26 the partially filled CNT case (Fig.7H). The unit cell volume appears to slightly decrease  
27 with the decrease of the temperature. Note however that the observed volume change  
28 is not comparable to that required for the observation of significant transitions in unit-  
29 cell magnetic moment values [28].  
30  
31

32  
33 In order to further verify this interpretation, additional comparative measurements were  
34 then performed on  $\text{Fe}_3\text{C}$  filled CNOs produced according with the method reported in  
35 ref.47 (see Fig.8 for typical TEM images) in a comparable temperature range (see also  
36 supp. Materials in ref.49 for comparative magnetization measurements). As shown in  
37 Figs.9-11 also in this case a weak contraction in the average unit cell volume of  $\text{Fe}_3\text{C}$   
38 and in the graphitic c-axis of the CNOs was found with the decrease of the temperature,  
39 with a small  $\text{Fe}_3\text{C}$  unit cell volume change of 0.27%.  
40  
41

42  
43 This observation appears to confirm the above interpretation and suggests the absence  
44 of  $\text{Fe}_3\text{C}$  unit cell induced magnetic moment transitions at low temperature in these types  
45 of materials. Instead, a crucial role in the appearance of the observed stepped  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

magnetization hysteresis appears to be taken by the faceted morphology of the nanowires. This observation is confirmed by direct comparison with other magnetization measurements performed in non-faceted Fe<sub>3</sub>C-filled CNOs, reported in ref.49; indeed, in this latter CNO-case an opposite trend involving a significant increase of the coercivity parameter with the decrease of the temperature was found.

## Conclusions

In conclusion in this work we have shown that MWCNTs filled with Fe<sub>3</sub>C nanowires can show unusual stepped-like hysteresis loops due to strain induced variation of the Fe<sub>3</sub>C nanowire volume. The origin of the observed stepped hysteresis was attributed to existence of antiferromagnetic-coupling in ferromagnetic faceted-interfaces. These findings open new avenues towards investigation of antiferromagnetism in faceted Fe<sub>3</sub>C filled CNTs systems for application in magnetic devices.

## Conflicts of interest

There are no conflicts of interest to declare

## Acknowledgments:

We are grateful for the financial support from the National Natural Science Foundation of China Grants Nos. 51671137, 11750110413 and 11950410752. We also acknowledge the analytical and testing center of Southwest Jiaotong University for the technical support in the magnetic measurements performed with SQUID.

## References

- [1] Mannini, M. et al. Quantum tunnelling of the magnetization in a monolayer of oriented single-molecule magnets. *Nature* 468, 417-422 (2010).
- [2] Mannini, M. et al. Magnetic memory of a single-molecule quantum magnet wired to a gold surface. *Nature Mater.* 8, 194–197 (2009).
- [3] Leuenberger, M. N. and Loss D. Quantum computing in molecular magnets. *Nature* 410, 789-93 (2001).
- [4] Bogani, L. and Wernsdorfer, W. Molecular spintronics using single-molecule magnets. *Nature Mater.* 7, 180-186 (2008).
- [5] Wernsdorfer, W. Molecular Magnets, a long-lasting phase. *Nature Mater.* 6, 174-176 (2007).
- [6] Mougel, V. et al. Uranium and manganese assembled in a wheel-shaped nanoscale single-molecule magnet with high spin-reversal barrier. *Nature Chem.* 4, 1012-1017 (2012).
- [7] Wernsdorfer, W. Molecular magnets: Chemistry brings qubits together. *Nature Nanotechnology* 4, 145 - 146 (2009).

- 1  
2  
3 [8] Ardavan, A. et al. Will spin-relaxation times in molecular magnets permit quantum  
4 information processing? *Phys. Rev. Lett.* 98, 057201 (2007).  
5  
6 [9] Urdampilleta, M. et al. Molecular Quantum Spintronics: Supramolecular Spin  
7 Valves Based on Single-Molecule Magnets and Carbon Nanotubes. *Int. J. Mol. Sci.*  
8 12, 6656-6667 (2011).  
9  
10 [10] Lv, R. et al. In situ synthesis and magnetic anisotropy of ferromagnetic buckypaper.  
11 *Carbon* 47, 1141-5 (2009).  
12  
13 [11] Weissker, U. et al. Perpendicular magnetization of long iron carbide nanowires  
14 inside carbon nanotubes due to magnetocrystalline anisotropy. *Journal of Applied*  
15 *Physics* 106, 054909 (2009).  
16  
17 [12] Hampel, S. et al. Growth and characterization of filled carbon nanotubes with  
18 ferromagnetic properties. *Carbon* 44, 2316-22 (2006).  
19  
20 [13] Morelos-Gomez, A. et al. Controlling high coercivities of ferromagnetic nanowires  
21 encapsulated in carbon nanotubes. *Journal of Material Chemistry* 20, 5906-5914 (2010).  
22  
23 [14] Leonhardt, A. et al. Synthesis and properties of filled carbon nanotubes. *Diamond*  
24 *and Related Materials* 12, 790-3 (2003).  
25  
26 [15] Prados, C. et al. Hysteresis shift in Fe-filled carbon nanotubes due to  $\square$ -Fe.  
27 *Physical Review B* 65, 113405 (2002).  
28  
29 [16] Wernsdorfer, W. et al. DC-SQUID magnetization measurements of single magnetic  
30 particles. *Journal of Magnetism and Magnetic Materials* 145, 33-39 (1995).  
31  
32 [17] Wernsdorfer, W. et al. Experimental Evidence of the Néel-Brown Model of  
33 Magnetization Reversal. *Physical Rev. Letters* 78, 1791- 1794 (1997).  
34  
35 [18] Chudnovsky, E. M. and Gunther, L. Quantum theory of nucleation in  
36 ferromagnets. *Physical Review B* 37, 9455-9459 (1988).  
37  
38 [19] Chudnovsky E. M. and Gunther L. Quantum Tunneling of Magnetization in Small  
39 Ferromagnetic Particles. *Physical Rev. Letters* 60, 661-664 (1988).  
40  
41 [20] Barbara, B and Wernsdorfer, W. Quantum tunneling effect in magnetic particles.  
42 *Current Opinion in Solid State & Materials Science* 2, 220-225 (1997).  
43  
44 [21] Wernsdorfer, W. et al. Nucleation of Magnetization Reversal in Individual  
45 Nanosized Nickel Wires. *Physical Rev. Letters* 77, 1873-1876 (1996).  
46  
47 [22] Buffat Ph. and Borel J-P. Size effect on the melting temperature of gold particles.  
48 *Phys. Rev. A* 13, 2287 (1976).  
49  
50 [23] Gangopadhyay S. et al. Magnetic properties of ultrafine iron particles. *Phys. Rev.*  
51 *B* 45, 9778 (1992).  
52  
53 [24] Tae-Jin Park et al. Size-Dependent Magnetic Properties of Single-Crystalline  
54 Multiferroic BiFeO<sub>3</sub> Nanoparticles. *Nano Lett.* 7, 766 (2007).  
55  
56 [25] L. Thomas et al. Macroscopic quantum tunnelling of the magnetization in a single  
57 crystal of nanomagnets. *Nature* 383, 145-147 (1996).  
58  
59 [26] Friedman, J. R. and Sarachik, M. P., Tejada J., Ziolo R. Macroscopic Measurement  
60 of Resonant Magnetization Tunneling in High-Spin Molecules. *Physical Review*  
*Letters* 76, 3830-3833 (1996).  
[27] Zhang, X. X. et al. Quantum tunnelling effects in Fe/Sm multilayers. I. *Phys.:*  
*Condens. Matter* 4, L1h3-L168 (1992).  
[28] Duman E. Magnetic Instabilities in Fe<sub>3</sub>C Cementite Particles Observed with Fe

1  
2  
3 K-Edge X-Ray Circular Dichroism under Pressure. *Physical Review Letters* 94, 075502  
4 (2005).

5  
6 [29] Hofer, L. J. E. and Cohn, E. M. Saturation Magnetization of Iron Carbides. 81,  
7 1576-1582 (1958).

8  
9 [30] Verdaguer, M. Molecular electronics emerges from molecular magnetism. *Science*  
10 272, 698–699 (1996).

11 [31] Rocha, A. R. et al. Towards molecular spintronics. *Nature Mater.* 4, 335–339 (2005).

12 [32] F. S. Boi, J. Guo, S. Wang, Y. He, G. Xiang, X. Zhang and M. Baxendale.  
13 Fabrication of cm scale buckypapers of horizontally aligned multiwalled carbon  
14 nanotubes highly filled with Fe<sub>3</sub>C: the key roles of Cl and Ar-flow rates. *Chem.*  
15 *Commun.*, 52, 4195 (2016).

16 [33] F.S.Boi, S. Maugeri, J. Guo, M. Lan, S. Wang, J. Wen, G. Mountjoy, Mark  
17 Baxendale, G. Nevill, R. M. Wilson, Y. He, S. Zhang, and G. Xiang. Controlling the  
18 quantity of  $\alpha$ -Fe inside multiwall carbon nanotubes filled with Fe-based crystals: The  
19 key role of vapor flow-rate. *Appl. Phys. Lett.*, 105, 243108 (2014).

20 [34] B. C. Satishkumar, A. Govindaraj, P. V. Vanitha, A. K. Raychaudhuri, and C. N. R.  
21 Rao, *Chem. Phys. Lett.* 362, 301 (2002).

22 [35] A. Taallah, M. Willis, J. Guo, J. Xia, M. Lan, S. Zhang, S. Wang, Y. He, G. Xiang  
23 and F. S. Boi. Observation of lamellar like fringes and Barkhausen effects in iron-  
24 carbon filled vertically aligned carbon nanotubes. *Journal of Applied Physics*, 124,  
25 214303 (2018).

26 [36] A Oiwa, A Endo, S Katsumoto, Y Iye, H Munekata. Staircase-like hysteresis loop  
27 in III–V compound diluted magnetic semiconductor (In,Mn)As at low temperatures.  
28 *Physica B: Condensed Matter*, 284–288, 1173-1174 (2000).

29 [37] Muttoni, G.. “Wasp-waisted” hysteresis loops from a pyrrhotite and magnetite-  
30 bearing remagnetized Triassic limestone. *Geophysical Research Letters* 22 3167  
31 (1995).

32 [38] L. H. Bennetta and E. Della Torre. Analysis of wasp-waist hysteresis loops. *Journal*  
33 *of Applied Physics* 97, 10E502 (2005).

34 [39] T. Magno de Lima Alves, B. Ferreira Amorim, M. Antonio Morales Torres, C.  
35 Gomes Bezerra, S. Nóbrega de Medeiros, P. Lana Gastelois, L. Eugenio Fernandez  
36 Outon and W. Augusto de Almeida Macedo. Wasp-waisted behavior in magnetic  
37 hysteresis curves of CoFe<sub>2</sub>O<sub>4</sub> nanopowder at a low temperature: experimental evidence  
38 and theoretical approach. *RSC Adv.*, 2017, 7, 22187-22196


39 [40] Roberts A. P., Cui Y., Verosub K. L., Wasp-waisted hysteresis loops: Mineral  
40 magnetic characteristics and discrimination of components in mixed magnetic systems.  
41 *Journal of Geophysical Research: Solid Earth*, 100 17909- 17924 (1995).

42 [41] Boi F. S., Zhang X. and Corrias A. Temperature driven structural-memory-effects  
43 in carbon nanotubes filled with Fe<sub>3</sub>C nano crystals. *Materials Research Express* 2018;  
44 5: 025010.


45 [42] Kumari, R.; Krishnia, L.; Kumar, V.; Singh, S.; Kotnala, R. K.; Juluri, R. R.; Bhatta,  
46 U. M.; Satyam, P. V.; Yadav, B. S.; Naqvi, Z.; and Tyagi, P. K.; Fe<sub>3</sub>C filled carbon  
47 nanotubes: permanent cylindrical nanomagnets possessing exotic magnetic properties.  
48 *Nanoscale* 2016, 8, 4299-4310.

49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60


- 1  
2  
3 [43] Karmakar, S.; Sharma, S. M.; Mukadam, M. D.; Yusuf, S. M.; and Sood, A. K.;  
4 Magnetic behaviour of iron-filled multiwalled carbon nanotubes. *Journal of Applied*  
5 *Physics* 2005, 97, 054306.  
6  
7 [44] Mühl, T.; Elefant, D.; Graff, A.; Kozhuharova, R.; Leonhardt, A.; Mönch, I.;  
8 Ritschel, M.; Simon, P.; Groudeva-Zotova, S.; and Schneider, C. M.; Magnetic  
9 properties of aligned Fe-filled carbon nanotubes. *Journal of Applied Physics* 2003, 93,  
10 7894.  
11  
12 [45] Mihalik jr. M., Mihalik M., Lazúrová J., Fitta M., Vavra M. Magnetic properties  
13 of NdMn<sub>1-x</sub>Fe<sub>x</sub>O<sub>3+δ</sub> system. *EPJ Web of Conferences* 2013; 40: 15007.  
14 [46] Wollan E. O. and Koehler W. C. Neutron Diffraction Study of the Magnetic  
15 Properties of the Series of Perovskite-Type Compounds [(1-x)La, xCa]MnO<sub>3</sub>. *Phys.*  
16 *Rev.* 1955;100: 545-63.  
17  
18 [47] F. S. Boi, J. Guo, G. Xiang, Mu Lan, S. Wang, J. Wen, S. Zhang and Y. He. Cm-  
19 size free-standing self-organized buckypaper of bucky-onions filled with ferromagnetic  
20 Fe<sub>3</sub>C. *RSC Adv.*, 2017, 7, 845.  
21  
22 [48] Hellwig O., Kirk T. L., Kortright J. B., Berger A. and Fullerton E. E. A new phase  
23 diagram for layered antiferromagnetic films. *Nature Materials* 2003; 2: 112-116.  
24 [49] Boi F. S., Ivaturi S., Wang S., Zhang X. Temperature driven structural transitions  
25 in the graphitic-arrangement of carbon onions filled with FePd<sub>3</sub> nano crystals. *Carbon*  
26 2017, 120: 392-96 (see supplementary materials of this reference for hysteresis loops  
27 and temperature dependent measurement of the magnetization of Fe<sub>3</sub>C-filled CNOs).  
28 [50] Tackett R. J., Bhuiya A. W. and Botez C. E. Dynamic susceptibility evidence of  
29 surface spin freezing in ultrafine NiFe<sub>2</sub>O<sub>4</sub> nanoparticles. *Nanotechnology* 2009; 20:  
30 445705.  
31 [51] Nagata S., Keesom P. H., Harrison H. R. Low-dc-field susceptibility of CuMn spin  
32 glass. *Physical Review B* 1979; 19: 1633-1638.  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

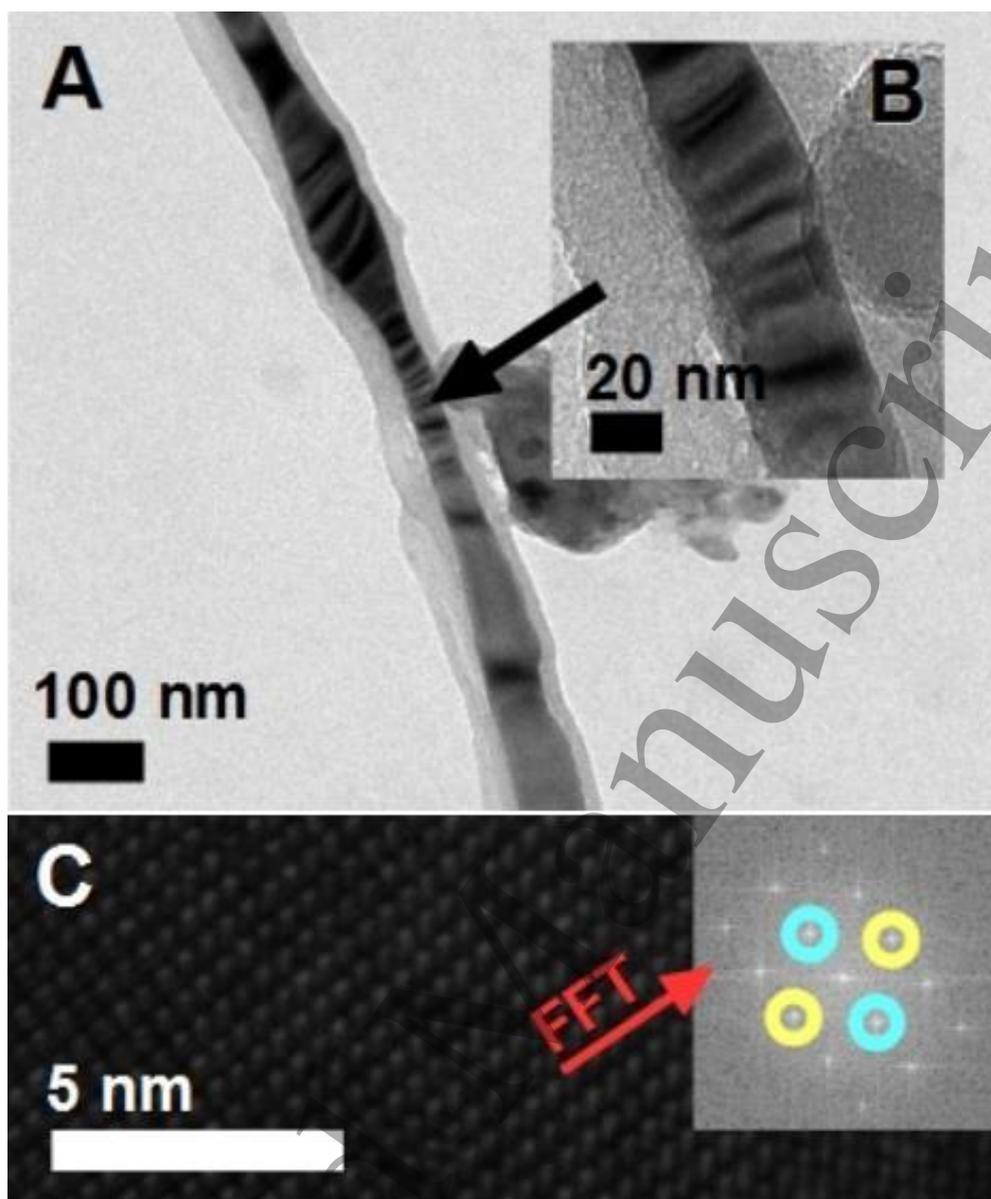


**Figure 1:** TEM (A-B) and HRTEM (C) micrographs of a typical Fe<sub>3</sub>C crystal encapsulated inside a MWCNT. The inset in C shows the reduced Fourier transform of the lattice (see text for lattice indexing).

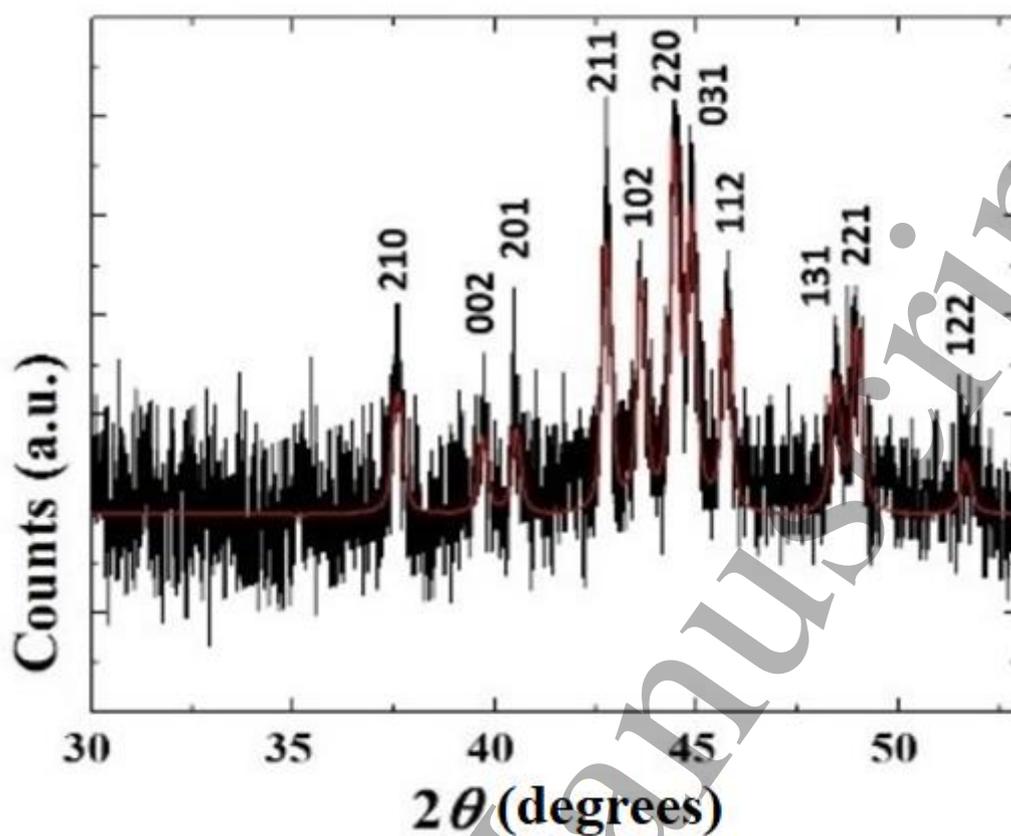


**Figure 2:** XRD pattern (acquired at  $\sim 298$  K) of a typical powder sample of MWCNTs filled with  $\text{Fe}_3\text{C}$  (unit cell volume of  $0.15706 \text{ nm}^3$ ). The red line represents the Rietveld refinement of the measured data (black line). Each peak is indicated with the corresponding lattice reflection

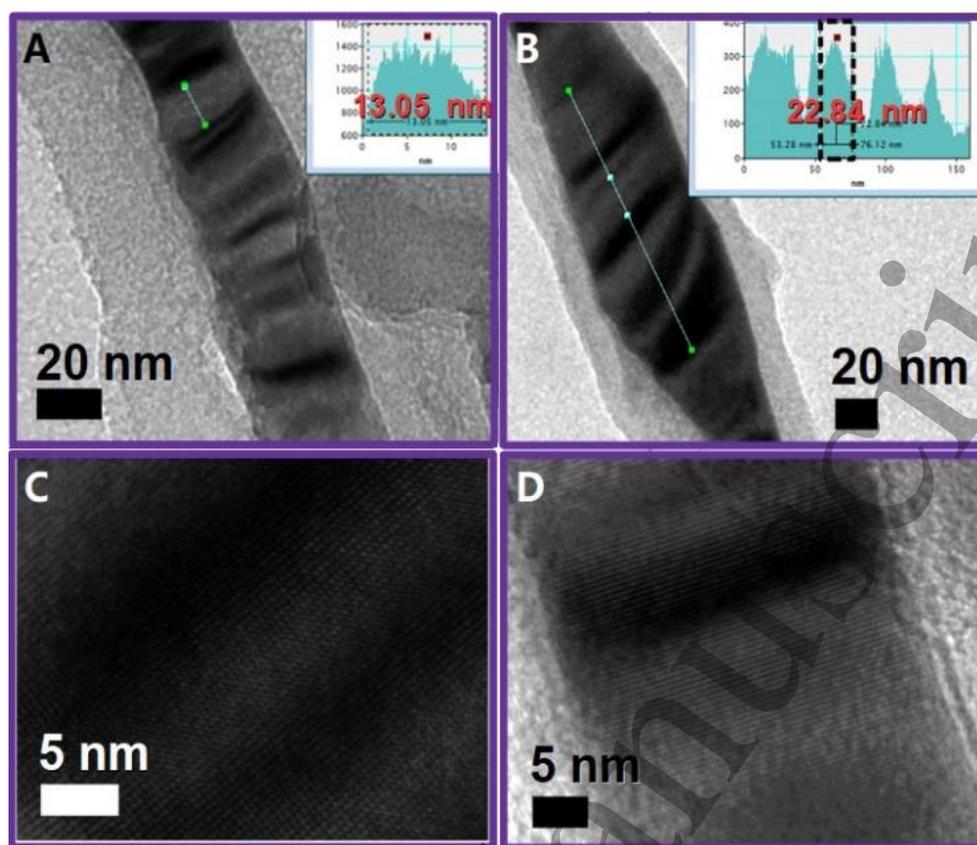


**Figure 3:** In A HRTEM micrograph of typical faceted Fe<sub>3</sub>C crystal inside a MWCNT. The inset profile analysis shows the size of a selected faceted-like area of the nanowire where a variation in the unit cell volume is found. Note the presence of repeated bright and dark areas implying existence of strain in the nanowire lattice, which could be at the origin of the formation of antiferromagnetic regions in the sample. In B HRTEM micrographs of another area of a typical Fe<sub>3</sub>C crystal inside the MWCNT. The inset profile analysis shows the size of a selected faceted-like area of the nanowire where a variation in the unit cell volume is found. Note also in this case the presence of repeated bright and dark areas implying existence of strain in the nanowire lattice. In C and D HRTEM micrographs showing other examples of faceted Fe<sub>3</sub>C crystals inside a MWCNT with atomic resolution.

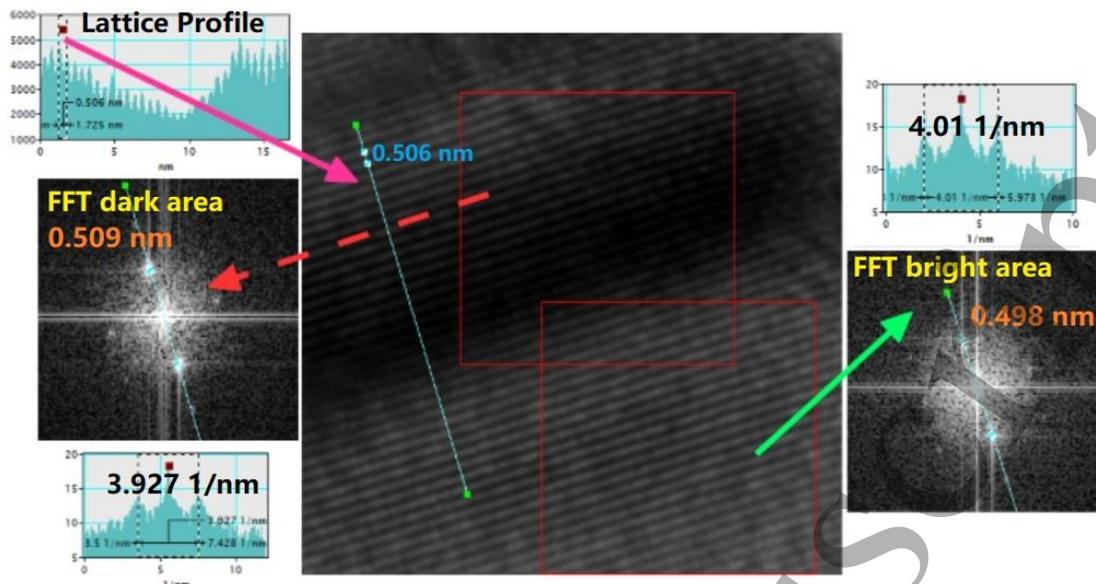


**Figure 4:** Profile analyses of the  $\text{Fe}_3\text{C}$  nanowire. Note the variation of the lattice parameters in the dark region (which represents a zone of nanowire bending) from the value of 0.498 nm to the value of 0.509 nm. Such lattice variation along the nanowire volume implies possible presence of multiple magnetic contributions to the observed hysteresis, as a consequence of nanowire localized lattice-stress in the faceted areas. Possible strain-induced formation of antiferromagnetic-ferromagnetic interfaces due to the fast cooling used in the experimental methods is suggested.

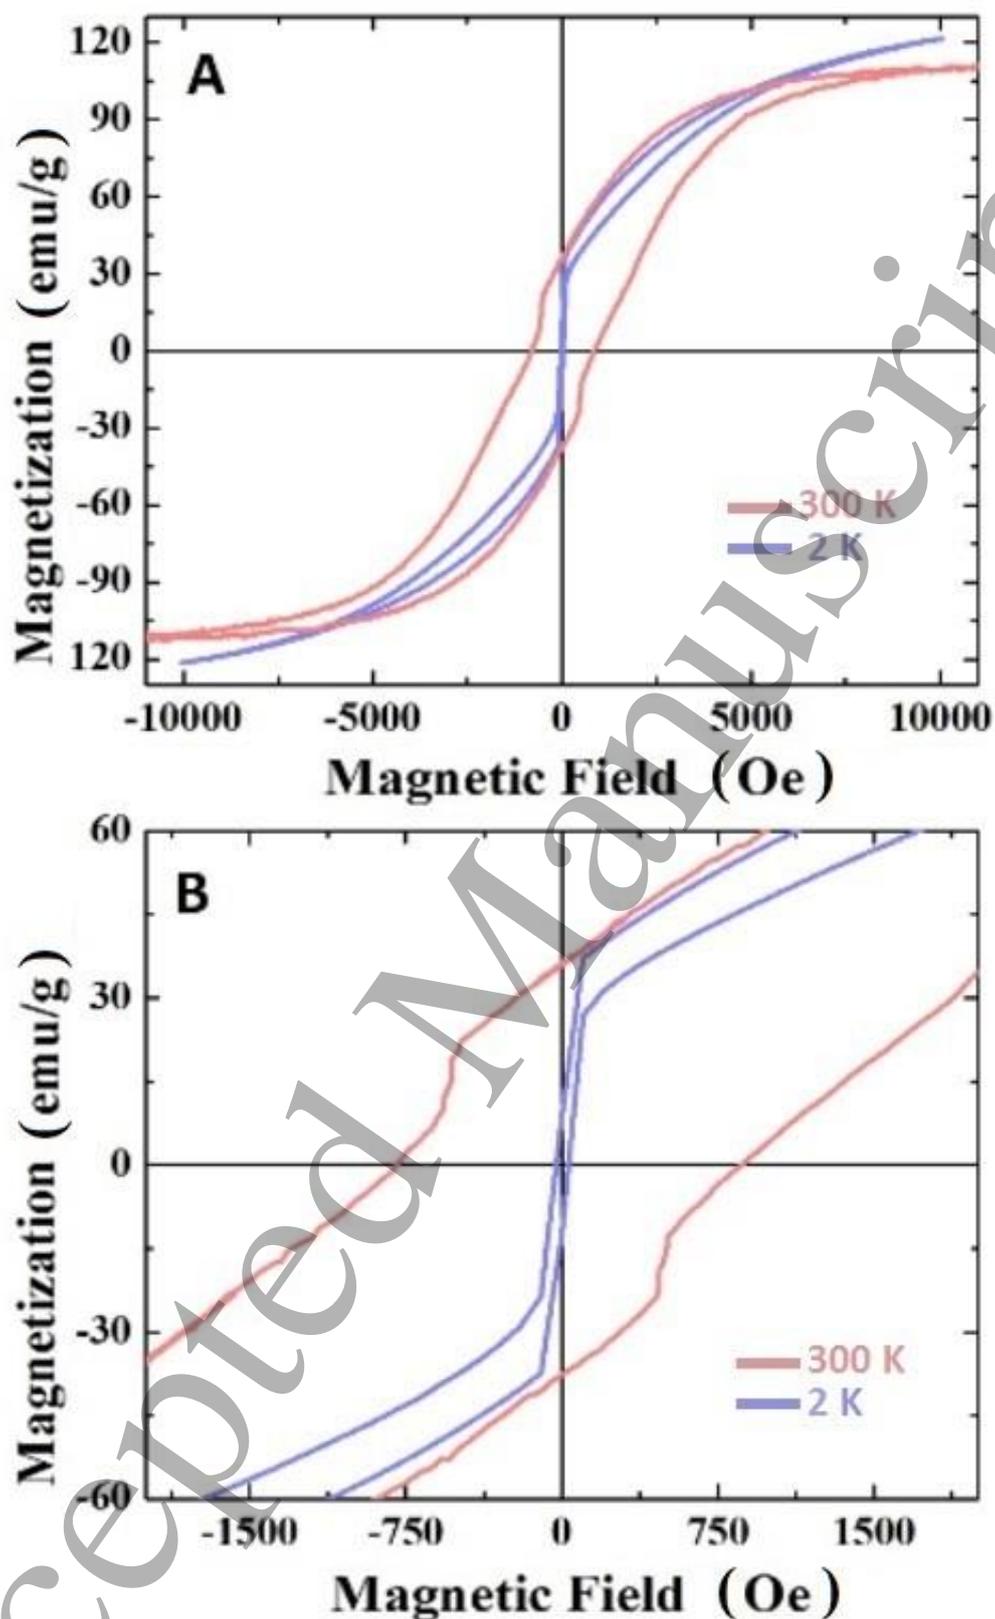


**Figure 5:** In A, ferromagnetic hysteresis acquired at 300 K (red-line) and 2 K (blue-line) from a powder of MWCNTs filled with  $\text{Fe}_3\text{C}$  nanowires with average unit cell volume of  $0.15706 \text{ nm}^3$  as determined via Rietveld refinement methods. The unusual collapse in the coercivity at low temperature is shown in B with a higher detail.

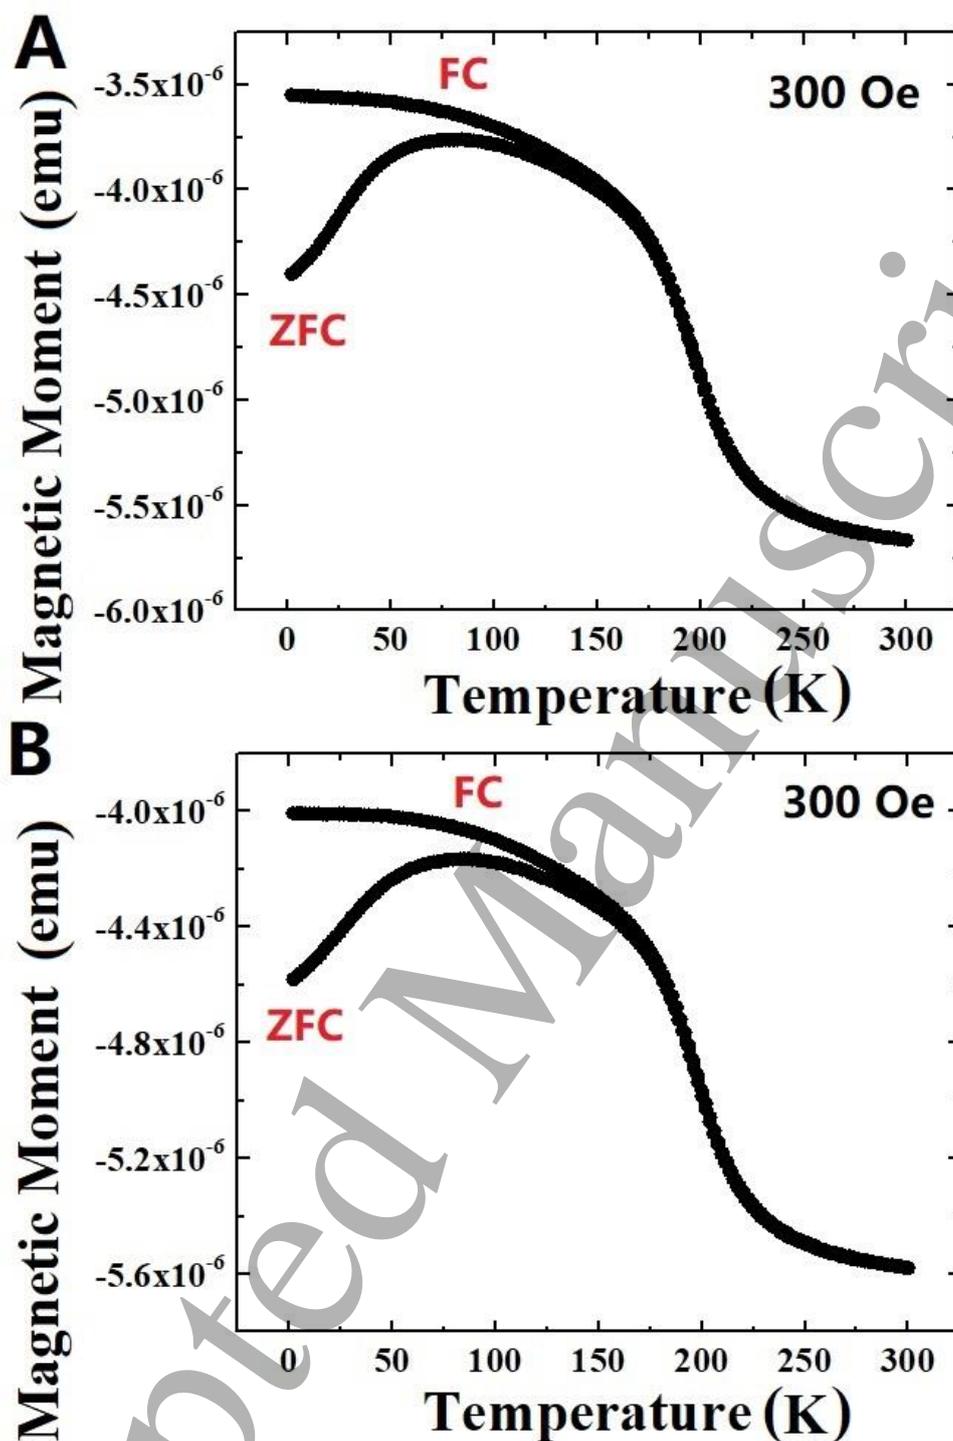


**Figure 6:** ZFC and FC magnetic curves in A and B, acquired from two different portions of the filled CNTs product. At  $\sim 70$  K it is noticeable the presence of a spin-glass-like behaviour possibly arising from competing ferromagnetic and antiferromagnetic interactions. It is also important to highlight the presence of a negative magnetic moment within all the temperature range.

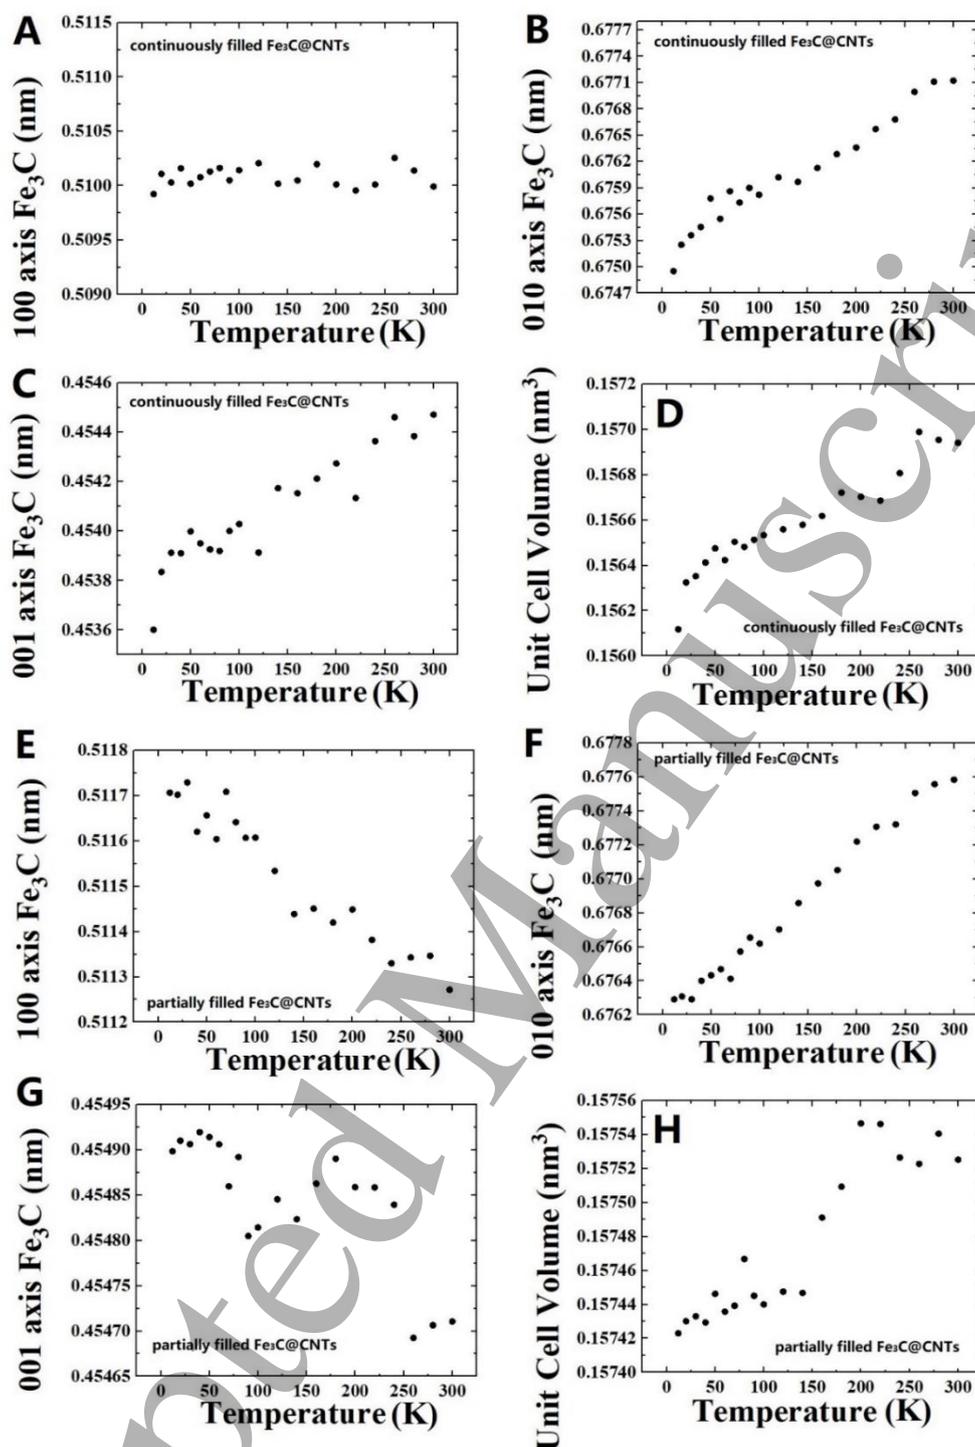


**Figure 7:** Plots showing the variation of the 100, 010, 001 axis values and of the unit-cell-volume of  $\text{Fe}_3\text{C}$  nanowires encapsulated continuously (A-D) and partially (E-H) inside the CNTs. This was determined via repeated Rietveld refinements performed on a narrower  $2\theta$  region of the XRD patterns reported in ref. 41. The improved quality of the refined data allowed for a more accurate estimation of the unit cell volume variation which appears to slightly decrease with the decrease of temperature in both cases. Note however that the observed change in unit cell volume values is not comparable to that required for the observation of significant transitions in magnetic moment values, as indicated in ref. [28,29]

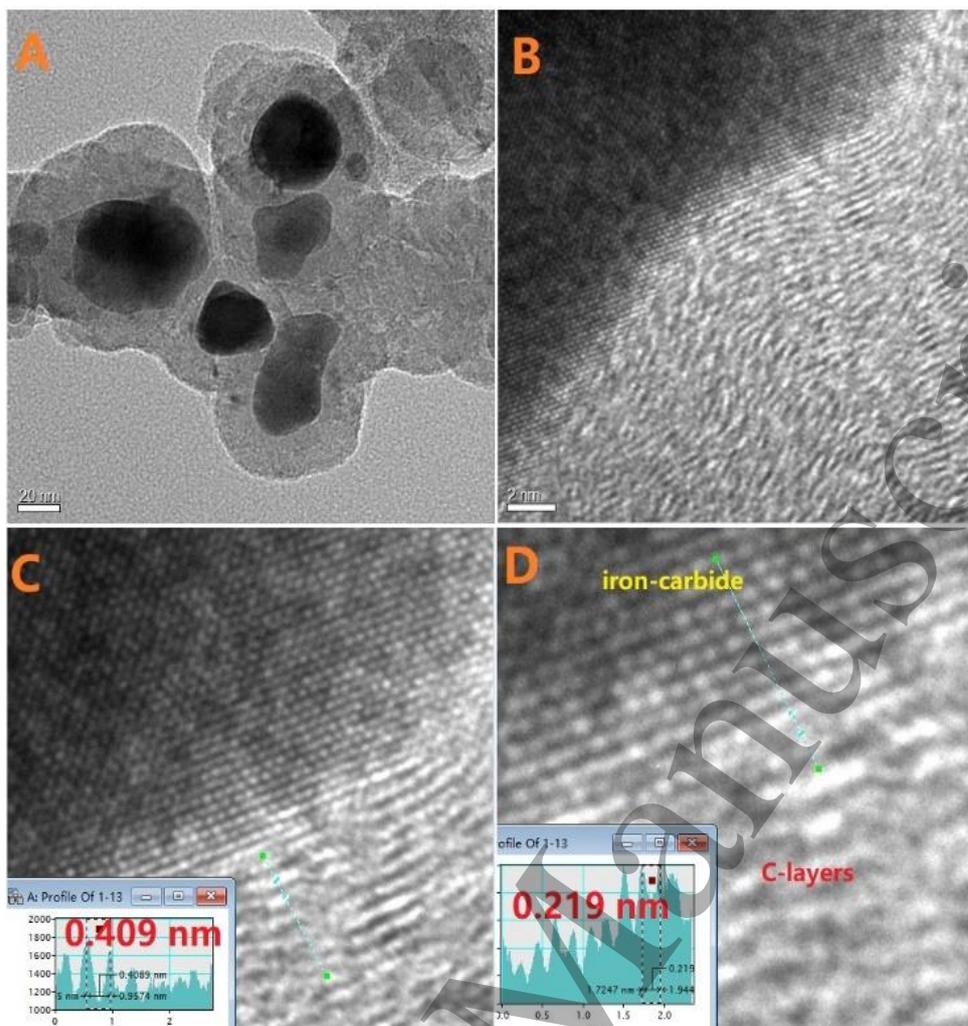


**Figure 8:** TEM micrograph shows the cross sectional of Fe<sub>3</sub>C@CNOs. In (D), the detail interface region of the Fe<sub>3</sub>C crystals and C layers is shown.

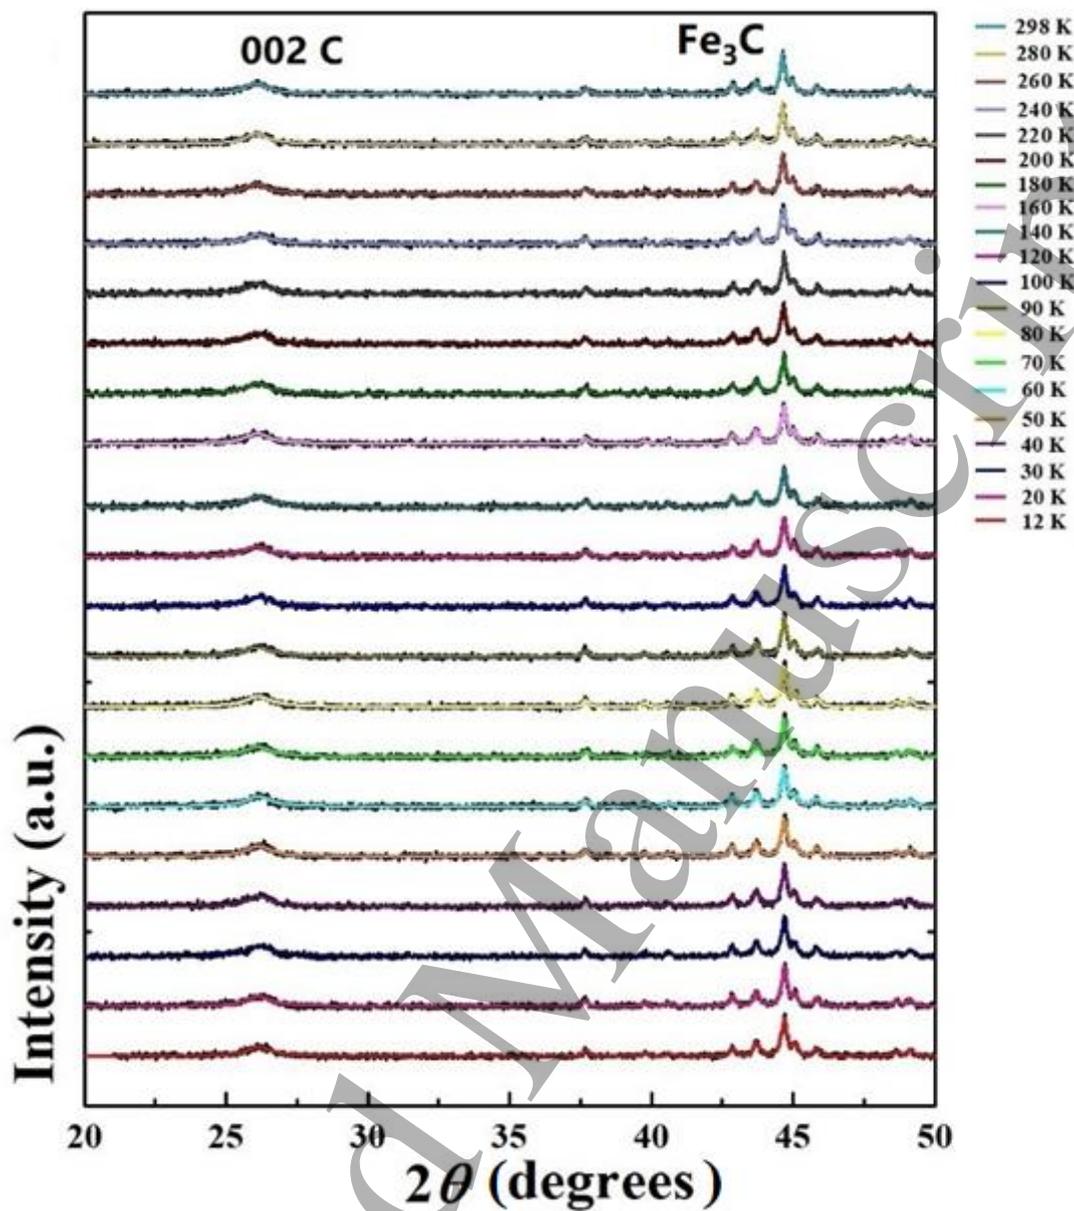

**Figure 9:** XRD patterns and Rietveld refinements (colored lines) in the temperature range from 12K to 298 K for the specific case of Fe<sub>3</sub>C filled CNOs.

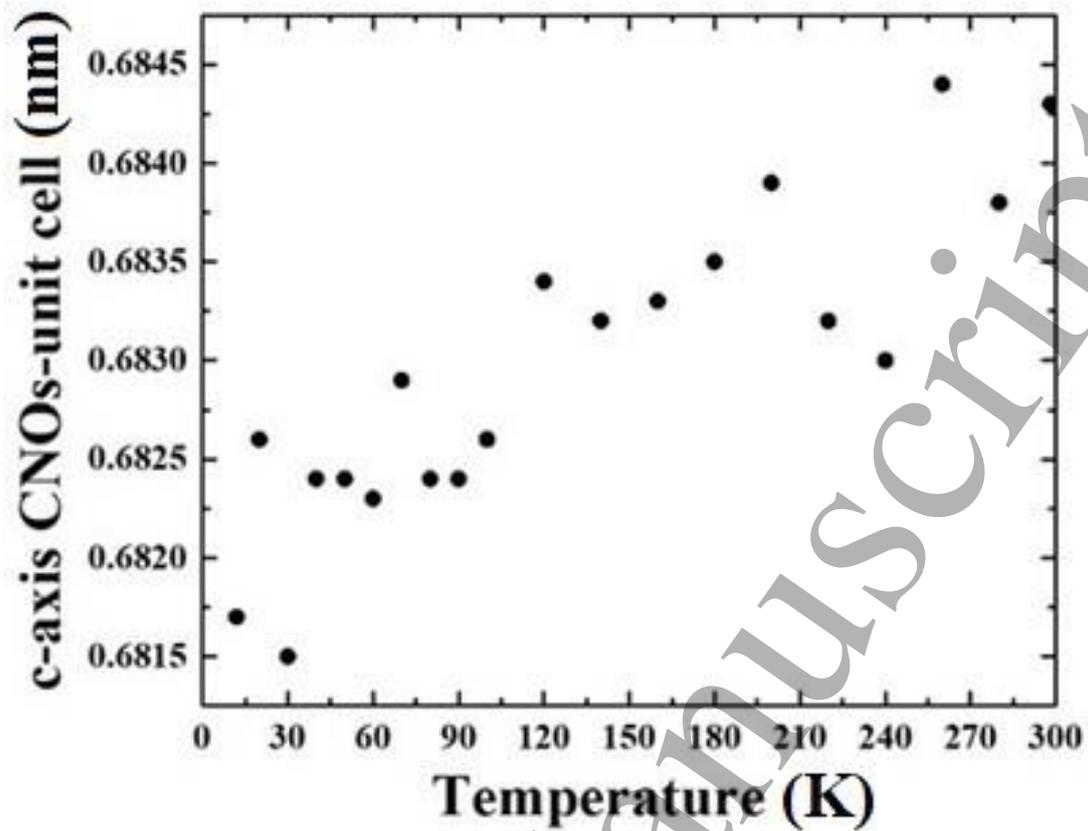

**Figure 10:** Plot showing the variation of the unit cell c-axis of CNOs as a function of the change of the temperature from 12K to 298 K. A contraction effect similar to that observed in ref. 41 is observed, with decreasing temperature.

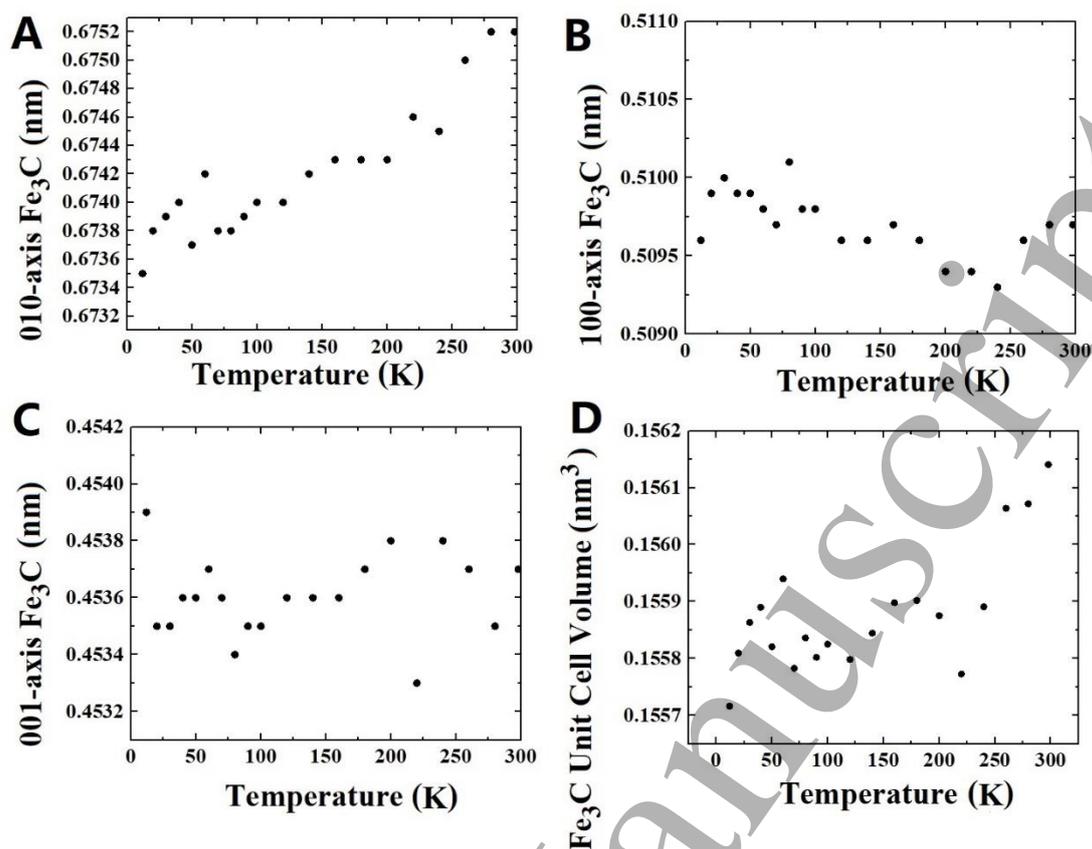

**Figure 11:** Plot showing the variation of the unit cell (010), (100), (001) axis and calculated unit cell volume of Fe<sub>3</sub>C filled CNOs by the change of the temperature from 12K to 298 K. A 0.32% average unit cell volume change is shown in (D) in the temperature range from 12K to 298K.