



Kent Academic Repository

Doheny, Patrick W., Chen, Jiasheng, Gruner, Thomas, Grosse, F. Malte and Saines, Paul J. (2023) *Dy(OH)3: A Paramagnetic Magnetocaloric for Hydrogen Liquefaction*. Journal of Materials Chemistry A . ISSN 2050-7488.

Downloaded from

<https://kar.kent.ac.uk/103951/> The University of Kent's Academic Repository KAR

The version of record is available from

<https://doi.org/10.1039/D3TA05358J>

This document version

Author's Accepted Manuscript

DOI for this version

Licence for this version

CC BY (Attribution)

Additional information

For the purpose of open access, the author(s) has applied a Creative Commons Attribution (CC BY) licence to any Author Accepted Manuscript version arising.

Versions of research works

Versions of Record

If this version is the version of record, it is the same as the published version available on the publisher's web site. Cite as the published version.

Author Accepted Manuscripts

If this document is identified as the Author Accepted Manuscript it is the version after peer review but before type setting, copy editing or publisher branding. Cite as Surname, Initial. (Year) 'Title of article'. To be published in **Title of Journal**, Volume and issue numbers [peer-reviewed accepted version]. Available at: DOI or URL (Accessed: date).

Enquiries


If you have questions about this document contact ResearchSupport@kent.ac.uk. Please include the URL of the record in KAR. If you believe that your, or a third party's rights have been compromised through this document please see our [Take Down policy](https://www.kent.ac.uk/guides/kar-the-kent-academic-repository#policies) (available from <https://www.kent.ac.uk/guides/kar-the-kent-academic-repository#policies>).

Journal of Materials Chemistry A

Materials for energy and sustainability

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: P. W. Doheny, J. Chen, T. Gruner, F. M. Grosse and P. J. Saines, *J. Mater. Chem. A*, 2023, DOI: 10.1039/D3TA05358J.

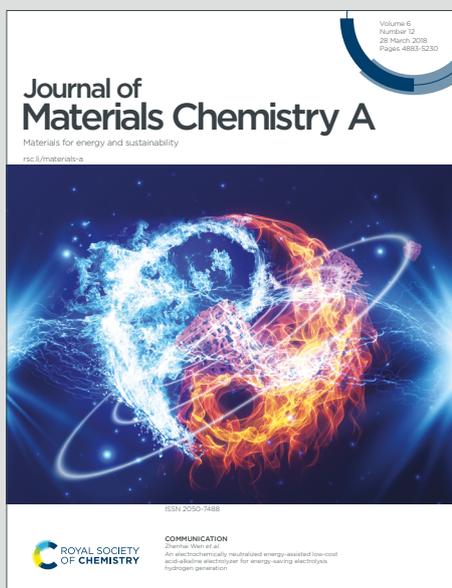

This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

ARTICLE

Dy(OH)₃: A Paramagnetic Magnetocaloric for Hydrogen LiquefactionPatrick W. Doheny,^a Jiasheng Chen,^b Thomas Gruner,^{b,c} F. Malte Grosche^b and Paul J. Saines^{*a}Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

The magnetic properties of a series of Ln(OH)₃ (where Ln = Gd-Er) coordination polymer materials have been examined to evaluate their potential as magnetocaloric materials. Dy(OH)₃ was found to exhibit an impressive magnetic entropy change of 33.4 J kg⁻¹ K⁻¹ at 12 K for a magnetic field change of 5-0 T, based on magnetisation measurements. Further magnetic heat capacity analysis indicated a maximum adiabatic temperature change of 8.4 K at 22.7 K. The favourable magnetocaloric parameters obtained for Dy(OH)₃ demonstrated its effectiveness to act as magnetic cooling material for hydrogen liquefaction, since the boiling point of hydrogen aligns well with the temperature for peak magnetocaloric performance of Dy(OH)₃ for high field changes.

Introduction

Low temperature cooling capabilities are essential for a number of diverse applications such as quantum computing, spintronics and medical imaging techniques that require cooling to temperatures well below 80 K.¹⁻³ Underlying these applications is the dependence on liquid cryogenics, particularly liquid helium, an expensive and finite resource.⁴ One specific application that requires cooling to these temperatures is hydrogen liquefaction, in which gaseous hydrogen is condensed to its liquid state by cooling to 20.15 K before the resulting liquid hydrogen is stored in pressurised, thermally insulated containers. This greatly increases the storage density of the fuel key to employing the hydrogen economy to decarbonise modern society, enabling more efficient hydrogen storage and transport.^{5, 6} Due to the very low boiling point of hydrogen, liquefaction processes typically require the use of cryogenics and a series of heat exchangers to condense the gas to its liquid state, the end result being an extended and energy-intensive process.⁷

An alternative to cryogen-assisted hydrogen liquefaction is that of a magnetocaloric-based liquefaction system in which magnetic materials utilising the magnetocaloric effect cool the feed gas to below the boiling point of liquid hydrogen; this would involve either using a sequence of magnetocalorics to cool from 77 K to 20 K or combining magnetocalorics with a cryocooler, whose efficiencies increase significantly towards the higher part of this temperature range.⁸⁻¹¹ This avoids the need for using liquid helium for low-temperature cooling and is more efficient than using a purely cryocooler-based system. The magnetocaloric effect refers to low temperature cooling obtained by placing paramagnetic materials in

a cycled magnetic field to facilitate an entropically driven solid-state cooling process.¹² The advantage of such magnetic refrigeration is the renewable and recyclable nature of the working material and elimination of the need for expensive and non-renewable helium as a refrigerant leading to much interest in magnetocaloric materials from both fundamental¹³⁻¹⁵ and applied perspectives.^{16, 17} Previously reported magnetocaloric materials have attained 60% of the ideal (Carnot) efficiency,¹⁸ but further improvements are required in the design and development of magnetocaloric materials before they can be employed as a practical alternative to conventional cryogen-based cooling methods. In order to maximise cooling efficiency, magnetocaloric materials must satisfy a number of design parameters, namely a dense structure with a high concentration of magnetic cations and large increases in magnetisation at low applied fields.

One class of materials capable of satisfying these requirements are coordination polymer materials in which small inorganic ligands, such as carbonates¹⁹ or hydroxides,²⁰ or simple organic ligands such as formate²¹ or oxalate²² can be used to synthesise structurally dense materials with a high concentration of magnetic ions.^{23, 24} Gd-based materials are the most heavily studied among magnetocalorics due to their high $S = 7/2$ spin number that leads to large magnetic entropy changes with the predicted maximum change given by $nR\ln(2S + 1)$. Despite this, the majority of Gd-based magnetocalorics are optimised for operation at ~2 K where, although magnetic entropy changes of 42.8-66.4 J kg⁻¹ K⁻¹ have been reported,²⁵⁻²⁷ increases in temperature lead to rapid decreases in magnetocaloric efficiency. Recently however, a number of materials have been reported that retain promising magnetocaloric properties up to 10 K through exploiting magnetic frustration arising from 1D chains of Ising spins within the crystal structure.^{14, 28-35}

Currently, materials that maintain favourable magnetocaloric properties at temperatures above 10 K are much less common. In most cases, magnetic entropy changes and hence, magnetocaloric performance, decrease with increasing temperature. Despite this, several examples of favourable magnetocaloric performance at

^a School of Chemistry and Forensic Science, Ingram Building, University of Kent, Canterbury, CT2 7NH, United Kingdom.

^b Cavendish Laboratory, University of Cambridge, Cambridge, CB3 0HE, United Kingdom.

^c SLB Cambridge Research, Cambridge, CB3 0EL, United Kingdom

† Corresponding author's email: P.Saines@kent.ac.uk

Electronic Supplementary Information (ESI) available. See DOI: 10.1039/x0xx00000x



higher temperatures have been reported, such as GdCrO_4 which shows a maximum magnetic entropy change of $29.0 \text{ J kg}^{-1} \text{ K}^{-1}$ at 22 K for a field change of 9.0 T^{36, 37} and GdCo_2B_2 which undergoes a maximum change of $21.5 \text{ J kg}^{-1} \text{ K}^{-1}$ at 25 K for a field change of 7.0 T,³⁸ while entropy changes of between 15 and $20 \text{ J kg}^{-1} \text{ K}^{-1}$ at ~ 20 K have been observed for similarly large field changes in other materials.³⁹⁻⁴² Several classes of materials such as various high entropy transition metal alloys and intermetallic $\text{RECo}_{12}\text{B}_6$ (where RE = Ce, Pr, Nd) materials have also achieved more modest magnetic entropy changes at temperatures ranging from 210-420 K^{43, 44} and 50-200 K⁴⁵ respectively. Compared to the high performance achieved at lower temperatures using more modest applied fields, this still leaves great scope for new magnetocaloric materials development at higher temperatures.

$\text{Ln}(\text{OH})_3$ coordination polymer materials are ideal candidates for high temperature magnetocaloric studies. They form in well characterised 3D hexagonal structures,⁴⁶ in which simple hydroxide ligands enable high magnetic density, and they have magnetic properties⁴⁷⁻⁵⁰ that are favourable to magnetocaloric performance at higher temperatures. The $\text{Ln}(\text{OH})_3$ series is known to crystallise as dense, 3D structures with hexagonal 1D channels (Figure 1b). The nine-coordinate $\text{Ln}(\text{III})$ ions (Figure 1a) are bridged by $\mu_3\text{-OH}^-$ ligands to form face-sharing polyhedra (Figure 1c) along the *c*-axis connected in an edge-sharing fashion within the *ab*-plane.

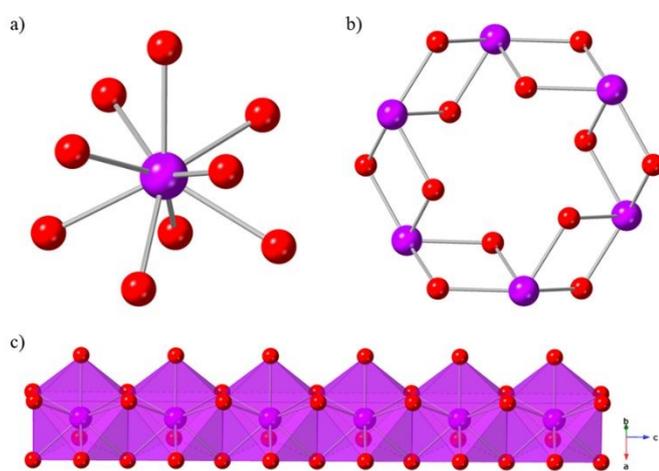


Figure 1. Crystal structure of $\text{Gd}(\text{OH})_3$ showing a) the nonacoordinate $\text{Gd}(\text{III})$ ion, b) the hexagonal channels viewed down the *c*-axis and c) 1D chains of $\text{Gd}(\text{III})$ face-sharing polyhedra. Atom labelling: Gd = purple and O = red. The hydrogen atoms have been omitted for clarity.

Ln-O bonds range from 2.437(8) and 2.452(14) Å in $\text{Gd}(\text{OH})_3$ to 2.402(4) and 2.439(6) Å in $\text{Er}(\text{OH})_3$ with the associated magnetic superexchange angles (Table S1) similarly ranging from $95.4(4)^\circ$ and $112.4(4)^\circ$ in $\text{Gd}(\text{OH})_3$ to $94.45(17)^\circ$ and $111.94(11)^\circ$ in $\text{Er}(\text{OH})_3$, which give the possibility of ferromagnetic coupling for the heavier lanthanides with Ising like-spins.⁴⁶ Consistent with this, while $\text{Gd}(\text{OH})_3$ is known to order antiferromagnetically at 1.7 K²⁰ and $\text{Er}(\text{OH})_3$ to remain paramagnetic down to 1.2 K,⁴⁷ the Tb, Dy and Ho analogues demonstrate ferromagnetic ordering with reported ordering temperatures of 3.7,⁴⁹ 3.5 and 2.5 K,⁵⁰ respectively. These

previous studies have also described the Ising-like spin behaviour of the Tb, Dy and Ho materials in which the spins are aligned along the *c*-axis with dominant interactions between adjacent Ln chains, properties favourable to the design of magnetocaloric materials.

Here, we examine the magnetocaloric properties of the $\text{Ln}(\text{OH})_3$ (Ln = Gd-Er) series of materials, using magnetisation and magnetic heat capacity methods to calculate the magnetic entropy and adiabatic temperature changes. Notably, while $\text{Tb}(\text{OH})_3$ and $\text{Ho}(\text{OH})_3$ maintain respectable performance over a 4-20 K temperature range, $\text{Dy}(\text{OH})_3$ shows an even larger magnetic entropy change of $28.0 \text{ J kg}^{-1} \text{ K}^{-1}$ at 20 K for a 5.0 T field change. To the best of our knowledge, this material displays the largest entropy change reported for a magnetocaloric per weight at 20 K for this field change. The material also demonstrates an excellent adiabatic temperature change, $-\Delta T_{ad}$, of 8.4 K at 22.7 K for a 5.0 T field change which is higher than those reported for other magnetocaloric materials such as $\text{ErCo}_2\text{Ni}_{0.17}\text{Al}_{0.03}$ ⁵¹ and GdCrO_4 .³⁷ Given its performance, $\text{Dy}(\text{OH})_3$ is a viable magnetocaloric cooling material for cooling at the relatively high temperature of 20 K for use in applications such as the final stage of a magnetocaloric based hydrogen liquefaction system.

Results and Discussion

Synthesis and Structure

Polycrystalline samples of the five $\text{Ln}(\text{OH})_3$ materials were synthesised using a hydrothermal reaction of the chosen $\text{Ln}(\text{NO}_3)_3 \cdot x\text{H}_2\text{O}$ and 20 M NaOH solution which was heated at 200 °C in a sealed reaction vessel for 72 hr. Powder X-ray diffraction analysis (Figures S1-S5) of the resulting solids confirmed the Gd, Tb, Dy, Ho and Er phases were all consistent with the previously reported hexagonal $P6_3/m$ $\text{Ln}(\text{OH})_3$ structures.⁴⁶

Magnetic Susceptibility and Magnetisation

The magnetic susceptibility properties of the $\text{Ln}(\text{OH})_3$ series were characterised using SQUID magnetometry over a 1.8-300 K temperature range under an applied field 1000 Oe (see Supplementary Information for experimental details). The magnetic susceptibility of the Gd and Er materials did not show any indications of long-range magnetic ordering down to 1.8 K while field cooled and zero field cooled susceptibility measurements of the Tb, Dy and Ho phases diverge at low temperatures, consistent with the ferromagnetic ordering previously reported for these materials (Figure S6-S10).^{49, 50} In order to identify the type of magnetic interactions present in these materials, the inverse susceptibility was fitted using the Curie-Weiss law (Figure S11-S15). The data was not fitted over the full 1.8-300 K temperature range, as the inverse susceptibility of the Tb-Er containing materials began to deviate from linearity at lower temperatures, likely in part due to crystal field effects. Instead, fits were carried out over both a high temperature range, where quenching of the orbital angular momentum by the weak crystal field of the lanthanides should not be significant, and a narrow low temperature range in which local linearity of the inverse susceptibility was maintained, which might be expected to give a better indication of the strength of magnetic interactions at these



temperatures. The resulting Weiss temperatures, θ_{CW} , obtained from fitting the Curie-Weiss law (Table 1), indicated the presence of ferromagnetic interactions in the Tb(OH)₃ and Dy(OH)₃ materials while the Weiss temperature of Gd(OH)₃ was consistent with antiferromagnetic interactions; the results obtained for the Gd, Tb and Dy phases are consistent with their ordered states at low temperatures.⁴⁷⁻⁵⁰ Surprisingly the θ_{CW} of Ho(OH)₃ is weakly negative

Table 1. Magnetic properties of the Ln(OH)₃ series where high temperature Curie-Weiss fits were performed over a temperature range of 100-300 K.

Ln	Expected μ_{eff} (μ_B)	High-T θ_{CW} (K)	High-T μ_{eff} (μ_B)	Low-T Fit (K)	Low-T θ_{CW} (K)	Low-T μ_{eff} (μ_B)
Gd	7.94	-1.10	7.62	10-50	-1.83	7.63
Tb	9.72	20.15	9.51	10-50	0.97	10.75
Dy	10.65	19.60	10.62	10-50	5.08	11.33
Ho	10.60	-2.55	10.40	20-50	-1.69	10.26
Er	9.58	3.67	9.58	18-50	-8.95	10.32

Isothermal magnetisation measurements at 4 K (Figure 2) revealed that the Tb, Dy and Ho materials underwent rapid magnetisation at low fields with only minor increases in magnetisation observed beyond an applied field of 20 kOe. In contrast, the Gd and Er phases displayed much more gradual magnetisation behaviour with saturation unobserved even at the maximum applied field of 50 kOe, consistent with strong antiferromagnetic interactions. The rapid increases in the Tb(OH)₃, Dy(OH)₃ and Ho(OH)₃ magnetisation with magnetic field at low temperature (Figures S16-S20) were attributed to ferromagnetic interactions allowing easy alignment with the applied field. This is supported by the $\chi_M T$ data (Figures S21-S25) which all show sustained increases in $\chi_M T$ on cooling to near 4 K before decreasing below about 3 K. This indicates the onset of a ferromagnetic transition near 4 K, consistent with previous reports.^{47, 53} The influence of strong antiferromagnetic interactions contributing to the gradual magnetisation of the Gd(OH)₃ and Er(OH)₃ is also consistent with the temperature dependence of $\chi_M T$, which decreases monotonically below 100 K in these materials.

Previous single crystal studies of the magnetic properties of lanthanide hydroxide materials have characterised the magnetic interactions of the Tb, Dy and Ho phases as indicative of anisotropic Ising-type systems, with spins aligned parallel to the *c*-axis and the dominant interactions found between linear chains of Ln nearest-neighbours.^{47, 49, 50} In comparison, the magnetic interactions of the Gd material are more consistent with a Heisenberg spin system characterised primarily by nearest-neighbour interactions within Gd chains and weak coupling between the chains, although non-trivial magnetic dipole interactions are also suggested to be present.⁴⁸

Using the Maxwell relation, $\Delta S_m(T) = \int [\partial M(T,B)/\partial T]_B dB$, the magnetocaloric properties of the Ln(OH)₃ series were evaluated by their magnetic entropy changes (Table 2) between 4-20 K and magnetic field changes of 1-0 and 5-0 T. The maximum entropy change, $-\Delta S_m^{max}$ of the series at 4 K for a 1-0 T field change (Figure 3a) was 20.3 J kg⁻¹ K⁻¹ measured in Tb(OH)₃, while Gd(OH)₃ showed the

over both temperature ranges, despite its ferromagnetic ordered state,⁵⁰ while the θ_{CW} of Er(OH)₃ changes from 3.67 K for the higher temperature fit to -8.95 K for the lower temperature fit. This may be a result of these materials having the highest orbital angular moments of the series and therefore being the most strongly influenced by crystal field effects.⁵²

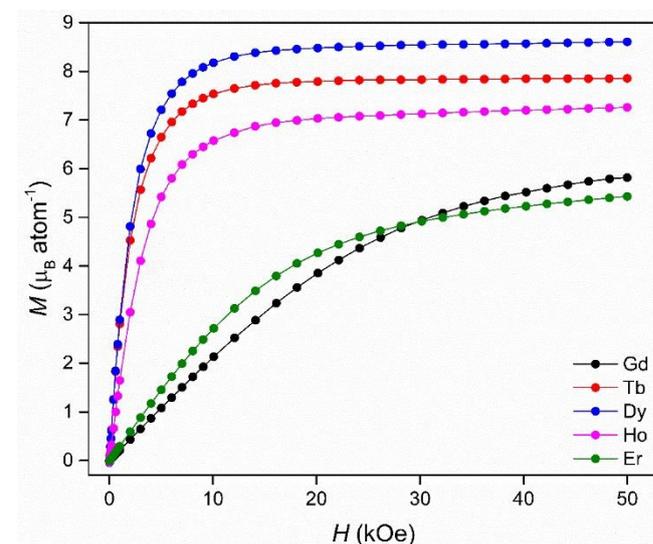


Figure 2. Isothermal magnetisation curves of the Ln(OH)₃ series at 4 K.

smallest $-\Delta S_m^{max}$ of the series at 3.9 J kg⁻¹ K⁻¹. The magnetic entropy changes for the Tb, Dy and Ho materials were characterised by rapid decreases with increasing temperature, consistent with the loss of spin alignment with the applied field due to increasing thermal fluctuations. The magnetic entropy changes for a 2-0 T field change (Figure S26, Table S2) for Tb and Ho also began decreasing with increasing temperature after 4 K while the Dy phase only underwent an incremental increase of 0.7 J kg⁻¹ K⁻¹. Notably Dy(OH)₃ underwent a slight increase to reach a $-\Delta S_m^{max}$ of 23.8 J kg⁻¹ K⁻¹ at 7 K before reaching a minimum of 9.1 J kg⁻¹ K⁻¹ at 20 K, substantially higher than that observed at 20 K for $\Delta B = 1-0$ T (cf. 2.7 J kg⁻¹ K⁻¹).

Table 2. Maximum entropy changes ($-\Delta S_m^{max}$) and peak temperatures (T_{max}) of the Ln(OH)₃ series at different field changes.

Ln	$\Delta B = 1-0$ T			$\Delta B = 5-0$ T		
	T_{max} (K)	$-\Delta S_m^{max}$ (J kg ⁻¹ K ⁻¹)	$-\Delta S_m^{max}$ (mJ cm ³ K ⁻¹)	T_{max} (K)	$-\Delta S_m^{max}$ (J kg ⁻¹ K ⁻¹)	ΔS_m^{max} (mJ cm ³ K ⁻¹)
Gd	4	3.9	21.1	4	43.7	239.9
Tb	4	20.3	113.4	5	26.8	150.0
Dy	4	19.4	112.4	12	33.4	193.4
Ho	4	17.5	103.8	9	28.7	170.5
Er	4	5.5	33.3	4	26.5	161.6

In contrast to the performance at low fields, at high fields (Figure 3b) the Gd(OH)₃ material displayed the largest magnetic entropy change of the series, with a $-\Delta S_m^{max}$ of 43.7 J kg⁻¹ K⁻¹ at 4 K followed by



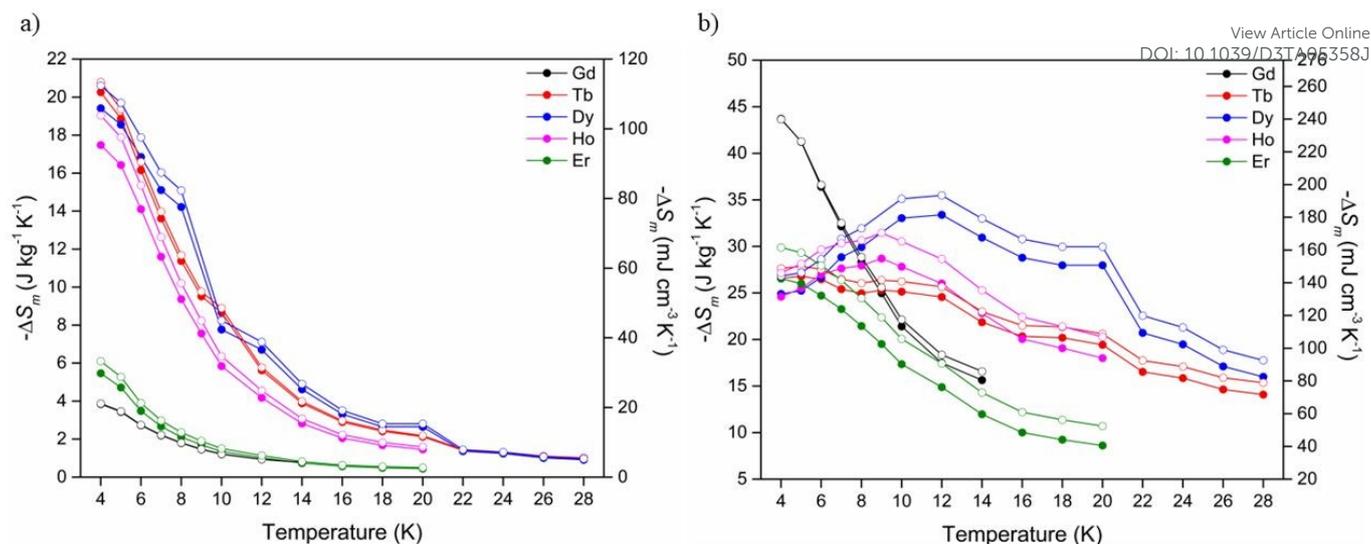


Figure 3. Magnetic entropy changes of the Ln(OH)₃ series for a) $\Delta B = 1.0$ T and b) $\Delta B = 5.0$ T. The filled and open symbols denote mass and volumetric entropy units respectively.

sustained decreases with increasing temperature. This is consistent with previous studies that reported a maximum magnetic entropy change of $50.1 \text{ J kg}^{-1} \text{ K}^{-1}$ for the Gd(OH)₃ phase at 2 K and $\Delta B = 7.0$ T.²⁰ The Er(OH)₃ material showed similar decreases with temperature in its magnetic entropy change with a maximum of $26.5 \text{ J kg}^{-1} \text{ K}^{-1}$ at 4 K followed by continued decreases with increasing temperature.

Unusually, the magnetic entropy changes for $\Delta B = 5.0$ T of Dy(OH)₃ and Ho(OH)₃ initially rise with increasing temperature, reaching a maximum of $33.4 \text{ J kg}^{-1} \text{ K}^{-1}$ and $28.7 \text{ J kg}^{-1} \text{ K}^{-1}$ at 12 and 9 K respectively. Tb(OH)₃ also showed a gradual decrease in entropy change up to 20 K such that its values for 5.0 T field changes at this temperature are comparable to Dy(OH)₃ and Ho(OH)₃, with all of these above $20 \text{ J kg}^{-1} \text{ K}^{-1}$. We anticipate that this likely stems from the ferromagnetic correlations within the paramagnetic phase of these materials as previously established for the ferromagnetic Ising chains

in A(HCO₂)₃ (A = Tb and Ho) and BOHCO₃ (B = Tb and Dy) with the higher temperature scale in these hydroxides resulting from the stronger magnetic interactions within them.^{14, 21, 33, 47, 49, 50, 54} Future studies of the hydroxides using modern neutron diffractometers to establish if they have magnetic diffuse scattering at these temperatures are needed to confirm this hypothesis.

Of the Ln(OH)₃ phases, Dy(OH)₃ has the most significant performance at temperatures that could be used for hydrogen liquefaction, retaining a value of $28.0 \text{ J kg}^{-1} \text{ K}^{-1}$ ($162.0 \text{ mJ cm}^{-3} \text{ K}^{-1}$) at 20 K. Additional measurements were made to higher temperatures, which showed that a magnetic entropy change of $16.0 \text{ J kg}^{-1} \text{ K}^{-1}$ was obtained even at 28 K. To the best of our knowledge, the highest performing magnetocaloric materials at around 20 K that have previously been reported are GdCrO₄ and GdCo₂B₂, which for a field change of 5.0 T have a $-\Delta S_m^{\text{max}}$ of $18.8 \text{ J kg}^{-1} \text{ K}^{-1}$ ($101.0 \text{ mJ cm}^{-3} \text{ K}^{-1}$)³⁶,

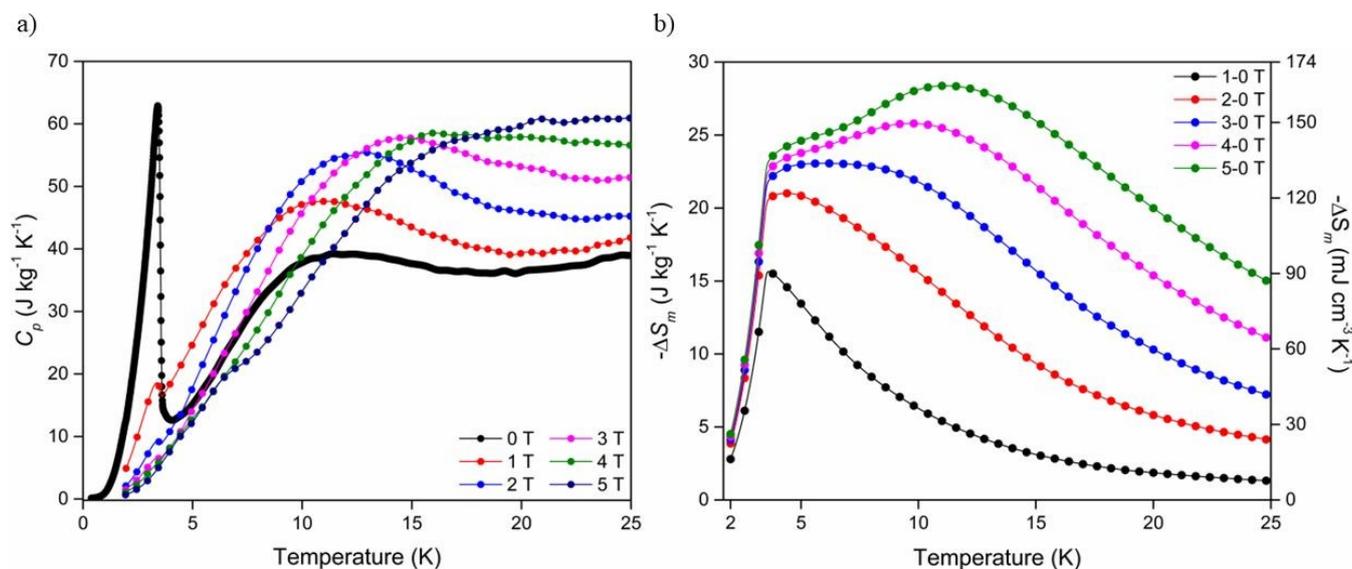


Figure 4. a) Specific heat capacity of Dy(OH)₃ at applied fields of between 0 and 5 T and b) magnetic entropy changes determined from heat capacity data for field changes up to $\Delta B = 5$ T.



³⁷ and $17.1 \text{ J kg}^{-1} \text{ K}^{-1}$ ($138.3 \text{ mJ cm}^{-3} \text{ K}^{-1}$)³⁸ at 22 K and 25 K, respectively. In terms of volumetric entropy changes, the $(\text{Er},\text{R}_{1-x})\text{Co}_2$ ($\text{R} = \text{Dy}, \text{Ho}$) series of materials⁵⁵ are also known to undergo large changes of $> 200 \text{ mJ cm}^{-3} \text{ K}^{-1}$, the magnitude and temperature range (20–80 K) of which can be further tuned *via* transition metal doping.⁵¹ It should be noted, however, that while these materials have very large volumetric entropy changes due to their high densities, their mass entropy changes are considerably smaller than $\text{Dy}(\text{OH})_3$ due to their much heavier formula unit.

Heat Capacity and Adiabatic Temperature Change

To investigate the entropy change of the $\text{Dy}(\text{OH})_3$ material further, heat capacity measurements of the polycrystalline sample were obtained over an applied field range of 5–0 T (see Supplementary Information for further details). At zero applied field, a large spike is observed in the specific heat capacity, C_p , at 3.41 K (Figure 4a) which was attributed to a ferromagnetic phase transition in line with previously reported data.⁵⁰ Consistent with this, increases in applied field strength led to a broadening of the transition peak while the transition temperature remains approximately constant. Integration of the heat capacity data, combined with a direct magnetocaloric measurement performed at 3 K (see Supplementary Information), allowed the derivation of the total entropy from the thermodynamic measurements (Figure S27) and the magnetic entropy changes up to $\Delta B = 5\text{-}0 \text{ T}$ (Figure 4b).

The temperature dependence of the magnetic entropy change obtained directly from the thermodynamic measurements is in line with that calculated indirectly from the magnetisation data, such that the maximum entropy change is shifted to higher temperatures with increasing magnetic field strength (Table S3). For $\Delta B = 1\text{-}0 \text{ T}$, a $-\Delta S_m^{\text{max}}$ of $15.6 \text{ J kg}^{-1} \text{ K}^{-1}$ ($90.6 \text{ mJ cm}^{-3} \text{ K}^{-1}$) was calculated at 3.6 K while, for $\Delta B = 5\text{-}0 \text{ T}$, a much higher $-\Delta S_m^{\text{max}}$ of $28.4 \text{ J kg}^{-1} \text{ K}^{-1}$ ($164.3 \text{ mJ cm}^{-3} \text{ K}^{-1}$) was obtained at 11.2 K. Despite the magnitude of the magnetic entropy changes calculated from both the magnetisation and heat capacity being consistent, a reduction of $\sim 15\%$ was observed in entropy changes determined from the heat capacity measurements relative to those determined from the magnetisation data ($28.4 \text{ vs. } 33.4 \text{ J kg}^{-1} \text{ K}^{-1}$ respectively for $\Delta B = 5\text{-}0 \text{ T}$). This apparent discrepancy may be attributed to the crystallites of the heat capacity sample deviating from 100% alignment with the magnetic easy axis (the c -axis), thus leading to the observed decrease in magnetic entropy change due to the higher fields required to magnetise the crystallites that deviate from alignment with the easy axis. This assumption is not unreasonable given the polycrystalline nature of the sample and known magnetic anisotropy of $\text{Ln}(\text{OH})_3$ materials. Correlations between magnetic entropy changes, sample alignment and applied magnetic field directions have previously been reported in materials with strong magnetic anisotropy.^{56–58} Regardless of the field change applied $-\Delta S_m$ decreases rapidly below 3.5 K, as would be anticipated since the emergence of long range ferromagnetic order will greatly decrease the entropy change under applied fields.

The thermodynamic data also allowed the adiabatic temperature change ($-\Delta T_{ad}$) of $\text{Dy}(\text{OH})_3$, the temperature change the material experiences when switching off the applied magnetic field under adiabatic conditions, to be calculated. This is determined directly

from Figure S27 as the temperature change at constant entropy between difference field curves. As with the magnetic entropy change, $-\Delta T_{ad}$ was found to have a strong magnetic field dependence (Figure 5) with the maximum $-\Delta T_{ad}$ shifting to higher temperatures with increasing magnetic field strength (Table S4). At a low field change of $\Delta B = 1\text{-}0 \text{ T}$, the maximum $-\Delta T_{ad}$ of 3.1 K was obtained at 6.8 K, while for a high field change of $\Delta B = 5\text{-}0 \text{ T}$, the maximum $-\Delta T_{ad}$ of 8.4 K was shifted to the far higher temperature of 22.7 K. In principle, this means that when held under a 5 T field at 22.7 K, removing the field will cause the material to cool by 8.4 K to 14.3 K. The $-\Delta T_{ad}$ of $\text{Dy}(\text{OH})_3$ is particularly promising compared to other materials that exhibit high ΔT_{ad} near 20 K for a similar 5–0 T field change e.g. about 6.5 K for $\text{ErCo}_{1.8}\text{Ni}_{0.17}\text{Al}_{0.03}$,⁵¹ 7 K for GdCo_2B_2 ³⁸ and 8 K for GdCrO_4 ,³⁷ amongst others (Table S5).

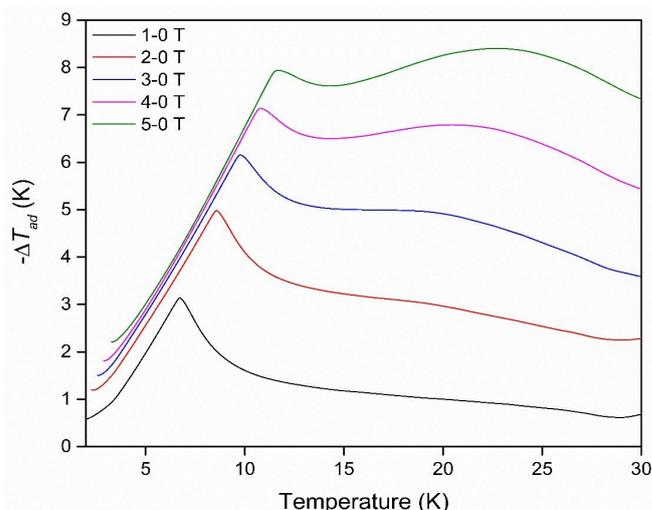


Figure 5. Adiabatic temperature changes of $\text{Dy}(\text{OH})_3$ for magnetic field change up to $\Delta B = 5\text{-}0 \text{ T}$.

This result again demonstrates the potential for the $\text{Dy}(\text{OH})_3$ material to act as a viable magnetocaloric at elevated temperatures, particularly for hydrogen liquefaction applications as both the $\text{Dy}(\text{OH})_3$ $-\Delta T_{ad}$ and $-\Delta S_m^{\text{max}}$ parameters at high field changes show favourable performance near the boiling point of hydrogen.

Conclusions

This study has examined the magnetic and magnetocaloric properties of five $\text{Ln}(\text{OH})_3$ materials (where $\text{Ln} = \text{Gd-Er}$) over a temperature range from 2 to 25 K. For low magnetic field changes, $\Delta B = 1\text{-}0 \text{ T}$, the magnetic entropy changes calculated from magnetisation measurements show $\text{Tb}(\text{OH})_3$ and $\text{Dy}(\text{OH})_3$ to be far superior than $\text{Gd}(\text{OH})_3$ despite their fewer unpaired spins, with the $-\Delta S_m^{\text{max}}$ of $20.3 \text{ J kg}^{-1} \text{ K}^{-1}$ calculated for the Tb material at 4 K which is over five times greater than the $-\Delta S_m^{\text{max}}$ of $3.9 \text{ J kg}^{-1} \text{ K}^{-1}$ for $\text{Gd}(\text{OH})_3$ at the same temperature. At high field changes, $\Delta B = 5\text{-}0 \text{ T}$, however, $\text{Dy}(\text{OH})_3$ demonstrated superior performance over a much wider temperature range compared to the other members of the series with a $-\Delta S_m^{\text{max}}$ that first increases with increasing temperature from $24.9 \text{ J kg}^{-1} \text{ K}^{-1}$ at 4 K to $33.4 \text{ J kg}^{-1} \text{ K}^{-1}$ at 12 K then gradually decreases beyond this such that a $-\Delta S_m$ of $16.0 \text{ J kg}^{-1} \text{ K}^{-1}$ is retained at 28 K.



The magnetocaloric properties of the Dy(OH)₃ material were examined further using thermodynamic measurements with a high field $-\Delta S_m^{\max}$ of 28.4 J kg⁻¹ K⁻¹ at 11.2 K recorded. The adiabatic temperature change was also determined from the heat capacity analysis with an $-\Delta T_{ad}$ of 8.4 K at 22.7 K determined for a $\Delta B = 5-0$ T field change, significantly higher than the $-\Delta T_{ad}$ of 3.1 K obtained for a field change of $\Delta B = 1-0$ T. This demonstrates Dy(OH)₃ as a promising magnetocaloric that can achieve a large temperature change around 20 K.

Given the favourable magnetocaloric properties, determined from both direct and indirect measurements, the potential for the Dy(OH)₃ material to be employed as a magnetic cooling material for moderate temperature applications has been demonstrated. One such application is in the hydrogen liquefaction process, as the boiling point of hydrogen (20.15 K) aligns well with the optimum magnetocaloric parameters determined for Dy(OH)₃ in this study making it very promising for the final stage of a magnetocaloric based liquefaction system.

Conflicts of interest

There are no conflicts to declare.

Author Contributions

The study was conceived by PJS in collaboration with FMG, with PJS and FMG responsible for funding acquisition and supervising the project team. Sample synthesis was performed by PWD who also collected and analysed the diffraction and magnetometry data. Heat capacity data were collected and analysed by JC and TG. PWD wrote the original draft of the manuscript with all authors reviewing and editing.

Acknowledgements

We would like to thank EPSRC for funding this research via grants EP/T027886/1 and EP/T028033/1.

References

1. T. D. Ladd, F. Jelezko, R. Laflamme, Y. Nakamura, C. Monroe and J. L. O'Brien, *Nature*, 2010, **464**, 45-53.
2. A. Hirohata, K. Yamada, Y. Nakatani, I.-L. Prejbeanu, B. Diény, P. Pirro and B. Hillebrands, *J. Magn. Magn. Mater.*, 2020, **509**, 166711.
3. L. Gyongyosi and S. Imre, *Comput. Sci. Rev.*, 2019, **31**, 51-71.
4. A. Cho, *Science*, 2009, **326**, 778-779.
5. A. M. Oliveira, R. R. Beswick and Y. Yan, *Curr. Opin. Chem. Eng.*, 2021, **33**, 100701.
6. M. van der Spek, C. Banet, C. Bauer, P. Gabrielli, W. Goldthorpe, M. Mazzotti, S. T. Munkejord, N. A. Røkke, N. Shah, N. Sunny, D. Sutter, J. M. Trusler and M. Gazzani, *Energy Environ. Sci.*, 2022, **15**, 1034-1077.
7. M. Aziz, *Energies*, 2021, **14**, 5917.
8. T. Numazawa, K. Kamiya, T. Utaki and K. Matsumoto, *Cryogenics*, 2014, **62**, 185-192. DOI: 10.1039/D3TA05358J
9. I. Park and S. Jeong, *Cryogenics*, 2017, **88**, 106-115.
10. I. Park and S. Jeong, *IOP Conf. Ser.: Mater. Sci. Eng.*, 2015, **101**, 012106.
11. T. Utaki, K. Kamiya, T. Nakagawa, T. A. Yamamoto and T. Numazawa, Boulder, Colorado, 2007.
12. A. Smith, *Eur. Phys. J. H*, 2013, **38**, 507-517.
13. M. Falsaperna and P. J. Saines, *Dalton Trans.*, 2022, **51**, 3394-3410.
14. R. J. C. Dixey and P. J. Saines, *Inorg. Chem.*, 2018, **57**, 12543-12551.
15. M. Wali, R. Skini, M. Khelifi, E. Dhahri and E. K. Hlil, *Dalton Trans.*, 2015, **44**, 12796-12803.
16. J. Lyubina, *J. Phys. D: Appl. Phys.*, 2017, **50**, 053002.
17. A. Kitanovski, *Adv. Energy Mater.*, 2020, **10**, 1903741.
18. V. Franco, J. S. Blázquez, B. Ingale and A. Conde, *Annu. Rev. Mater. Res.*, 2012, **42**, 305-342.
19. Y.-C. Chen, L. Qin, Z.-S. Meng, D.-F. Yang, C. Wu, Z. Fu, Y.-Z. Zheng, J.-L. Liu, R. Tarasenko, M. Orendáč, J. Prokleška, V. Sechovský and M.-L. Tong, *J. Mater. Chem. A*, 2014, **2**, 9851-9858.
20. Y. Yang, Q.-C. Zhang, Y.-Y. Pan, L.-S. Long and L.-S. Zheng, *Chem. Commun.*, 2015, **51**, 7317-7320.
21. P. J. Saines, J. A. M. Paddison, P. M. M. Thygesen and M. G. Tucker, *Mater. Horiz.*, 2015, **2**, 528-535.
22. S.-D. Han, X.-H. Miao, S.-J. Liu and X.-H. Bu, *Chem. Asian J.*, 2014, **9**, 3116-3120.
23. M. Kurmoo, *Chem. Soc. Rev.*, 2009, **38**, 1353-1379.
24. G. Mínguez Espallargas and E. Coronado, *Chem. Soc. Rev.*, 2018, **47**, 533-557.
25. Y.-C. Chen, F.-S. Guo, Y.-Z. Zheng, J.-L. Liu, J.-D. Leng, R. Tarasenko, M. Orendáč, J. Prokleška, V. Sechovský and M.-L. Tong, *Chem. Eur. J.*, 2013, **19**, 13504-13510.
26. G. Lorusso, J. W. Sharples, E. Palacios, O. Roubeau, E. K. Brechin, R. Sessoli, A. Rossin, F. Tuna, E. J. L. McInnes, D. Collison and M. Evangelisti, *Adv. Mater.*, 2013, **25**, 4653-4656.
27. E. Palacios, J. A. Rodríguez-Velamazán, M. Evangelisti, G. J. McIntyre, G. Lorusso, D. Visser, L. J. de Jongh and L. A. Boatner, *Phys. Rev. B*, 2014, **90**, 214423.
28. P. Mukherjee and S. E. Dutton, *Adv. Funct. Mater.*, 2017, **27**, 1701950.
29. N. D. Kelly, C. Liu and S. E. Dutton, *J. Solid State Chem.*, 2020, **292**, 121640.
30. P. W. Doheny, S. J. Cassidy and P. J. Saines, *Inorg. Chem.*, 2022, **61**, 4957-4964.
31. N. D. Kelly and S. E. Dutton, *Inorg. Chem.*, 2020, **59**, 9188-9195.
32. R. J. C. Dixey, F. Orlandi, P. Manuel, P. Mukherjee, S. E. Dutton and P. J. Saines, *Philos. Trans. R. Soc., A*, 2019, **377**, 20190007.
33. R. J. C. Dixey, G. B. G. Stenning, P. Manuel, F. Orlandi and P. J. Saines, *J. Mater. Chem. C*, 2019, **7**, 13111-13119.
34. P. Mukherjee, Y. Wu, G. I. Lampronti and S. E. Dutton, *Mater. Res. Bull.*, 2018, **98**, 173-179.
35. T. Numazawa, K. Kamiya, T. Okano and K. Matsumoto, *Phys. B: Condens. Matter*, 2003, **329-333**, 1656-1657.
36. A. Midya, N. Khan, D. Bhoi and P. Mandal, *J. Appl. Phys.*, 2014, **115**, 17E114.
37. E. Palacios, C. Tomasi, R. Sáez-Puche, A. J. Dos santos-



- García, F. Fernández-Martínez and R. Burriel, *Phys. Rev. B*, 2016, **93**, 064420.
38. L. Li, K. Nishimura and H. Yamane, *Appl. Phys. Lett.*, 2009, **94**, 102509.
39. J. Head, P. Manuel, F. Orlandi, M. Jeong, M. R. Lees, R. Li and C. Greaves, *Chem. Mater.*, 2020, **32**, 10184-10199.
40. R. Li, G. Li and C. Greaves, *J. Mater. Chem. A*, 2018, **6**, 5260-5264.
41. S. Pakhira, C. Mazumdar and R. Ranganathan, *J. Magn. Magn. Mater.*, 2019, **484**, 456-461.
42. L. Li and M. Yan, *J. Mater. Sci. Technol.*, 2023, **136**, 1-12.
43. Y. Zhang, P. Xu, J. Zhu, S. Yan, J. Zhang and L. Li, *Mater. Today Phys.*, 2023, **32**, 101031.
44. Y. Zhang, W. Hao, C. Hu, X. Wang, X. Zhang and L. Li, *Adv. Funct. Mater.*, 2023, **n/a**, 2310047.
45. Z. Ma, P. Xu, J. Ying, Y. Zhang and L. Li, *Acta Mater.*, 2023, **247**, 118757.
46. G. W. Beall, W. O. Milligan and H. A. Wolcott, *J. Inorg. Nucl. Chem.*, 1977, **39**, 65-70.
47. W. P. Wolf, H. Meissner and C. A. Catanese, *J. Appl. Phys.*, 1968, **39**, 1134-1136.
48. A. T. Skjeltop, C. A. Catanese, H. E. Meissner and W. P. Wolf, *Phys. Rev. B*, 1973, **7**, 2062-2091.
49. C. A. Catanese, A. T. Skjeltop, H. E. Meissner and W. P. Wolf, *Phys. Rev. B*, 1973, **8**, 4223-4246.
50. C. A. Catanese and H. E. Meissner, *Phys. Rev. B*, 1973, **8**, 2060-2074.
51. X. Tang, H. Sepehri-Amin, N. Terada, A. Martin-Cid, I. Kurniawan, S. Kobayashi, Y. Kotani, H. Takeya, J. Lai, Y. Matsushita, T. Ohkubo, Y. Miura, T. Nakamura and K. Hono, *Nat. Commun.*, 2022, **13**, 1817.
52. S. Cotton, *Lanthanide and Actinide Chemistry.*, Wiley, Hoboken, 2006.
53. H. E. Meissner and W. P. Wolf, *J. Appl. Phys.*, 1969, **40**, 1038-1038.
54. R. J. C. Dixey, P. Manuel, F. Orlandi, P. Mukherjee, S. E. Dutton, G. B. G. Stenning and P. J. Saines, *J. Mater. Chem. C*, 2020, **8**, 12123-12132.
55. Y. Zhu, K. Asamoto, Y. Nishimura, T. Kouen, S. Abe, K. Matsumoto and T. Numazawa, *Cryogenics*, 2011, **51**, 494-498.
56. H. Zhang, C. Xing, H. Zhou, X. Zheng, X. Miao, L. He, J. Chen, H. Lu, E. Liu, W. Han, H. Zhang, Y. Wang, Y. Long, L. van Eijk and E. Brück, *Acta Mater.*, 2020, **193**, 210-220.
57. N. Maraytta, J. Voigt, C. Salazar Mejía, K. Friese, Y. Skourski, J. Perßon, S. M. Salman and T. Brückel, *J. Appl. Phys.*, 2020, **128**.
58. P. Konieczny, D. Czernia and T. Kajiwara, *Sci. Rep.*, 2022, **12**, 16601.

View Article Online
DOI: 10.1039/D3TA05358J

