



Kent Academic Repository

Wosu, Chiziezi I., Harvey, Patricia J and Trivedi, Vivek (2024) *Nanoencapsulation of carotenoid extract via the temperature-induced phase transition of triblock polymer in Supercritical Carbon dioxide (scCO₂)*. RPS Pharmacy and Pharmacology Reports, 3 (1).

Downloaded from

<https://kar.kent.ac.uk/104573/> The University of Kent's Academic Repository KAR

The version of record is available from

<https://doi.org/10.1093/rpsppr/rqad035>

This document version

Author's Accepted Manuscript

DOI for this version

Licence for this version

CC BY (Attribution)

Additional information

Versions of research works

Versions of Record

If this version is the version of record, it is the same as the published version available on the publisher's web site. Cite as the published version.

Author Accepted Manuscripts

If this document is identified as the Author Accepted Manuscript it is the version after peer review but before type setting, copy editing or publisher branding. Cite as Surname, Initial. (Year) 'Title of article'. To be published in **Title of Journal**, Volume and issue numbers [peer-reviewed accepted version]. Available at: DOI or URL (Accessed: date).

Enquiries

If you have questions about this document contact ResearchSupport@kent.ac.uk. Please include the URL of the record in KAR. If you believe that your, or a third party's rights have been compromised through this document please see our [Take Down policy](https://www.kent.ac.uk/guides/kar-the-kent-academic-repository#policies) (available from <https://www.kent.ac.uk/guides/kar-the-kent-academic-repository#policies>).

**Nanoencapsulation of carotenoid extract *via* the temperature-induced phase transition
of triblock polymer in Supercritical Carbon dioxide (scCO₂)**

Chiziezi I. Wosu^a, Patricia J Harvey^a, Vivek Trivedi^{*b}

^aUniversity of Greenwich, Faculty of Engineering and Science, Central Avenue, Chatham Maritime, Kent, ME4 4TB, UK;

^bMedway School of Pharmacy, University of Kent, Central Avenue, Chatham Maritime, Kent, ME4 4TB, UK

chiziezi.wosu@gmail.com, V.Trivedi@kent.ac.uk, P.J.Harvey@greenwich.ac.uk

* Corresponding author: Dr Vivek Trivedi, Email: V.Trivedi@kent.ac.uk

© The Author(s) 2023. Published by Oxford University Press on behalf of the Royal Pharmaceutical Society.

This is an Open Access article distributed under the terms of the Creative Commons Attribution License (<https://creativecommons.org/licenses/by/4.0/>), which permits unrestricted reuse, distribution, and reproduction in any medium, provided the original work is properly cited.

Abstract

Objectives: Carotenoids are increasingly explored as nutraceuticals but their low bioavailability due to poor aqueous solubility limits their applications. This study discusses the development of a novel and organic solvent-free method to develop carotenoid-containing polymeric nanoparticles via temperature-induced phase transition (TIPT) of pluronic F-68 to obtain formulations with the improved dissolution of carotenoids.

Methods: The nanoencapsulation of carotenoids in pluronic F-68 was performed in supercritical carbon dioxide (scCO₂) to avoid oxidative or temperature/solvent-induced degradation. The nanoencapsulates were prepared in scCO₂ at 40 or 60 °C and 10 MPa without the aid of any organic solvent. The formulations thereafter were characterised for particle size via dynamic light scattering (DLS), particle morphology via Scanning Electron Microscopy (SEM) and carotenoid content/release via high-performance liquid chromatography (HPLC).

Key findings: HPLC results showed carotenoid degradation to be negligible in freshly prepared formulations when prepared in scCO₂ at 60 °C and 10 MPa. The developed particles were spheroidal with sizes ranging between 150-250 nm depending on carotenoid content in the preparation. An improvement in the aqueous solubility and storage stability (5 °C) of carotenoids was also observed for the formulations prepared in scCO₂.

Conclusions: These results suggest that TIPT under scCO₂ can be applied to formulate nanoparticulates with improved dissolution rate and stability of thermosensitive molecules such as carotenoids without causing any degradation during the processing.

Keywords: Carotenoid; Polymer Nanoparticles; carotenoid bioavailability; supercritical CO₂; HPLC; Temperature-induced phase transition

Introduction

In the food industry, β -carotene is primarily applied as a food colourant but there is a growing demand for β -carotene-based food, drinks, and beverages with the increasing interest in nutraceuticals [1,2]. Carotenoids are natural pigments comprising eight isoprene units joined to a skeleton of 40 carbon atoms. These are classified as oxygen-containing (xanthophylls, e.g., lutein, astaxanthin, cryptoxanthin etc) and hydrocarbons (carotenes, e.g., α -, β - carotene, lycopene etc). The antioxidant properties of carotenoids are known to provide numerous health benefits from the regulation of various bodily functions to acting as anti-inflammatory agents. Their applications in the treatment and management of cardiovascular, ophthalmological, pulmonary, cancer prevention, and neurodegenerative disorders are reported by numerous researchers [3,4].

Carotenoids are a vital component of human nutrition due to their important biological functions and these are regularly used as colourants, antioxidant supplements, and precursors of aroma or flavour compounds [5,6]. Due to these reasons, there is a clear interest in the food, chemical, pharmaceutical, cosmetics, personal care, and nutraceutical sectors in utilising carotenoids for various applications, as functional and/or bioactive compounds. Animals including humans cannot synthesise them in the body so these must be included in the diet. The bioavailability of carotenoids obtained from natural sources differs significantly due to matrix variability, poor intestinal absorption, and their limited aqueous solubility [1]. The applications of carotenoids remain limited because of their low bioavailability and stability concerns [7–9]. The discussion around the bioavailability of carotenoids is important as the only viable option to introduce them into the body is as dietary supplements [10]. Although, fruits and vegetables are good sources of carotenoids, their limited bioaccessibility of around 10% of total ingested carotenoids is a major constraint and matrix variability of plant sources also makes effective carotenoid dosing difficult to achieve [1,11]. Hence,

solubility and/or dissolution rate improvement of carotenoids is essential to enhance their bio-efficiency and expand their applications. Furthermore, carotenoids are also highly sensitive to temperature changes, organic solvents and stresses normally applied in traditional formulation development processes. This study aims to identify an effective, solvent-free, and novel approach to enhance the stability and aqueous solubility of carotenoids.

Nanoencapsulation is currently being increasingly explored to preserve the nutritional and bioactive properties and solubility of hydrophobic compounds in the pharmaceutical and food industries [1]. Nanoencapsulation involves coating a compound with a suitable material at the nanoscale (10 – 1000 nm) to produce particles with greater surface area per mass [12]. The formulation of carotenoids loaded in lipid-based nanoparticles such as solid lipid nanoparticles (SLNs), nanostructured lipid carriers (NLCs) and micelles have been widely explored in recent years [13–16]. These formulations typically involve thermal treatments at atmospheric pressure or require organic solvents during formulation, which could cause the degradation of carotenoids. Polymer-based encapsulation may offer an alternative and is increasingly used to develop delivery systems in the pharmaceutical and food industries [12]. In general, polymer-based encapsulation offers high stability, high encapsulation efficiency and controlled release of encapsulated compound [17]. A diverse range of polymers either of biological origin (e.g., albumin, chitosan, dextran, gelatine, phospholipids etc) or synthetic (e.g., polylactides (PLA), polyglycolide (PGA) and block co-polymers) can be used to develop stable and controlled release formulations [18–21].

PEG is a polymer of choice in drug delivery systems, and it is also commonly used in the food and cosmetic industries [22]. It is a synthetic, hydrophilic, and biocompatible polymer that is synthesised via ring-opening polymerisation of ethylene oxide to obtain a broad range of molecular weights and geometries. It is a USFDA-approved excipient, and its popularity principally stems from its tuneable properties and favourable safety profile. Pluronic (trade

name of poloxamers supplied by BASF) are triblock polymers consisting of hydrophobic polypropylene oxide (PPO) core with hydrophilic chains of polyethylene oxide (PEO) on each side [23]. Pluronic F-68 is a semi-crystalline polymer with a molecular weight of 8400 g/mol, containing on average 152 PEO and 29 PPO units [24]. Pluronics are listed excipients in the US and British Pharmacopoeias, considered generally regarded as safe (GRAS) and commonly used in the development of novel formulations [25–27]. Pluronics have various applications in food and pharma industries including as emulsifiers, dispersants, thickeners, and antifoaming/wetting agents [28–30]. Nanoencapsulation in this study was obtained using poloxamer or Pluronic and polyethylene glycol (PEG), structures of both are presented in Figure 1.

Figure 1. Generalised structure of a PEO-PPO-PEO triblock (A) polymer (x and y represent the length of PEO and PPO blocks, respectively) and polyethylene glycol (B).

Traditionally, polymeric nanoparticles are prepared via solvent-based processes usually involving the injection of an organic phase (e.g., polymers or triglycerides and the compound of interest in low boiling point solvents like acetone or ethanol) into an aqueous phase containing water and a surfactant under stirring. scCO_2 -associated processes such as supercritical emulsions extraction (SEE) are also being explored for micro/nanoparticle formation containing sensitive molecules [31]. These processes require organic solvent/s and are commonly performed in batch mode. The recent advancements in the continuous-SEE to prepare nanoparticles reproducibly have made it more attractive but the use of a solvent in this process is unavoidable [32–37]. Nonetheless, encapsulates prepared via continuous-SEE showed high encapsulation efficiency along with improved stability and antioxidant activity [38,39]. There are a few solvent-free processes such as one reported by Sang *et al* for nanoencapsulation by temperature-induced phase transition (TIPT) of Pluronic F-68 [40]. In this study, authors reported that heating a mixture of Pluronic F-68 and drug solution in PEG

400 to 120 °C followed by sudden cooling to 0 °C resulted in TIPT of the polymer and the obtained mass produced well-dispersed nanoencapsulates when suspended in water. TIPT results from the phase separation of copolymers at the nanometric scales caused by the incompatibility of different blocks within a copolymer (e.g., ABA (PPO-PEO-PPO) triblock polymers also commonly known as Pluronics). However, the high temperature required to obtain nanoparticles in the method is not suitable to develop formulations containing carotenoids due to the thermal degradation of these compounds [41]. Pluronic F-68 has a melting temperature of 55 °C at atmospheric pressure and PEG 400 is a liquid at room temperature. Significant to this study, Bhomia *et al* studied the effect of pressure on the solid-liquid transition of pluronics in pressurised CO₂ and observed a substantial decrease (35 °C at 100 bar) in their melting point in comparison to their actual melting point at atmospheric pressure [24]. The melting point depression caused by the dissolution of CO₂ in the polymer along with the prospect of working in an environment that is free from atmospheric water and oxygen can be favourable for the processing of sensitive molecules such as carotenoids at considerably low temperatures. The dissolution of CO₂ in polymer to produce a melt followed by spraying of the melt through a nozzle is commonly used for the particle formation in the process known as particles from the gas-saturated solution or PGSS [42]. This study utilises the capability of CO₂ to dissolve within pluronic to allow TIPT to occur at lower temperatures than 120 °C as used previously for the encapsulation of paclitaxel. However, it cannot be classed as PGSS because spraying of the melt was not performed for the particle formation. Hence, this study entails the development of nano-encapsulates via TIPT containing carotenoid extracts in scCO₂ at considerably low temperatures to avoid thermal, oxidative, hydrolytic and/or solvent-based degradation of carotenoid.

Materials and Methods

Materials

The extracts and reagents used in this study were used without any further purification. Extracts of *Dunaliella* biomass prepared using supercritical CO₂ were obtained from Hopfenveredlung St. Johann GmbH (NATECO₂), Munich, Germany. Pluronic F-68 and Polyethylene glycol 400 (PEG) were purchased from Sigma Aldrich Ltd, Gillingham (Dorset), UK. High-Performance Liquid Chromatography (HPLC) grade ethanol, Methyl-tert-butyl-ether (MTBE), methanol and HPLC vials were purchased from Fisher Scientific UK Ltd, Loughborough, UK. Liquid carbon dioxide with 99.9% purity was supplied by BOC Ltd. The standards of *All-trans* β-carotene, α-carotene, lutein, zeaxanthin, and phytoene were purchased from Sigma-Aldrich Inc. (Merck KGaA, Darmstadt, Germany).

Preparation of carotenoid-loaded pluronic nanoparticles

Carotenoid-loaded pluronic nanoparticles were prepared by TIPT. The method used for the preparation of carotenoid-polymeric nanoparticles (Car-PNPs) was adapted from the study published by Sang *et al* but modified such that nanoparticles were prepared in scCO₂ [40]. Car-PNPs were assigned descriptors based on formulation conditions as presented in Table 1. The carotenoid extract (5-20 wt % of total polymers) was thoroughly mixed with PEG under stirring at 200 rpm to form a sample-loaded phase. Subsequently, Pluronic F-68 was added under gentle mixing and the carotenoid extract-polymer blend was processed in an instrument (Thar Technology Inc., USA) detailed in Figure 2.

Figure 2: Schematic presentation of SCF instrument [CO₂ cylinder (A), chiller (B), CO₂ pump (C), high pressure vessel (RV), automatic back pressure regulator (ABPR), temperature controller (D) and display unit (E)].

The instrument consisted of a temperature controlled 150 mL high-pressure vessel with sapphire windows to visualise the experiment during processing. The temperature change in

the vessel was achieved via cartridge heaters operated by a temperature controller. A beaker containing the mixture was placed in the high-pressure vessel and heated at temperatures specified in Table 1 either at atmospheric pressure or under pressurised CO₂ (10 MPa). The processing temperature and pressure were chosen according to the study published by Bhomia *et al* [24]. The mixture was kept at a specified temperature and pressure for 90 min before cooling it by switching the heat off and performing a sudden depressurisation within 2 minutes or by leaving it in an ice bath (samples prepared at 0.1 MPa) to induce phase transition. The exit port on the vessel was fitted with 0.45 µm frit to avoid possible loss of particles in the process. No spillage of the contents in the beaker was observed in the high-pressure vessel after depressurisation. The beaker was then removed from the vessel and the processed material was gently crushed prior to being stored at 5 °C in an amber-coloured vial until required. Each preparation consisted of polymers in the ratio of 1:4 (PEG: pluronic F-68), except Car-PNP-1s which was prepared by mixing pluronic F-68 directly with the carotenoid extract in the absence of PEG. Each formulation was prepared in triplicate to ensure reproducibility. The nanoparticulates' preparation process is schematically depicted in Figure 3.

Figure 3: Schematic representation of the nanoparticulates' preparation process.

Carotenoid quantification

Carotenoids from the crude extract and formulations were extracted in ethanol by solid-liquid sonication method. 5 mg of extract or Car-PNPs containing an equivalent amount of carotenoids was suspended in 10 mL ethanol by gentle mixing prior to sonication and vortexing for 1 min each. After sonication, each sample was centrifuged at 3,000 g for 10 min at 15 °C and then the supernatants were filtered (0.45 µm filter) into amber-coloured HPLC vials. Samples were analysed by HPLC using an Agilent 21000 series HPLC equipped with a YMC₃₀ (250 x 4.9 mm I.D, S- 5 µm) analytical column and diode array detector (DAD).

Ethanol extracts (20 μ l) were analysed at 25 °C under an isocratic elution (mobile phase- 80% MeOH: 20% MTBE) at a flow rate of 1 mL min⁻¹. Carotenoids were quantified by reference to standards after separation by HPLC. Based on the quantification results, it was decided to investigate Car-PNP-1s further due to consistently high values for all studied carotenoids.

Particle size of carotenoid-loaded pluronic nanoparticles

The formulations were analysed to determine the average size and polydispersity index (PDI) of the nanoparticles. The average diameter and size distribution of the Car-PNPs were measured via dynamic light scattering (DLS) using a Zetasizer Nano-ZS (Malvern Instruments Ltd., UK). 50 mg of Car-PNP-1s or physical mixture (containing 10% w/w carotenoid extract) was dispersed in 10 mL of deionised water and sonicated for 2 minutes to produce well-dispersed nanoparticles in the media. 2 minutes of sonication was found to be sufficient to disperse taken mass which also provided reproducible particle size results. Measurements were conducted in triplicate at room temperature and the average particle size was presented as the mean of three measurements.

Morphology of carotenoid loaded Pluronic nanoparticles

The shape and surface morphology of the nanoparticles was determined using Scanning Electron Microscopy (SEM). 1 μ l of the nanoparticle suspension was placed on a microgrid coated with a thin carbon film and the excess liquid was removed by capillary action. The grid was vacuum-dried overnight forming a monolayer of the sample. The stub (12 mm diameter, Agar Scientific, G3347N) was mounted onto the sample holder and placed inside the Hitachi triple detector CFE-SEM SU8030 (Hitachi Triple detector CFE-SEM SU8030, (Roland Schmidt, Hitachi High-Technologies Europe, Germany) scanning electron

microscope. Micrographs were obtained using the upper secondary electron detector at a voltage of 1.0 kV.

Aqueous solubility and stability

The aqueous solubility of carotenoids was determined on carotenoid extract, Car-PNP-1s, and a physical mixture. An accurately weighed extract or Car-PNP/physical mixture containing 5 mg of carotenoids was weighed into a vial containing 10 mL of distilled water. The mixture was sonicated for 2 minutes to obtain well-formed nano-dispersion. It was then stirred at 200 rpm for 60 minutes and centrifuged thereafter at 3,000 g for 10 min. The HPLC analysis on the filtered (0.45 μm filters) supernatant was performed (method detailed in section 2.2.2) at 25 °C using a YMC₃₀ column and under an isocratic elution (mobile phase-80% MeOH: 20% MTBE) at a flow rate of 1 mL min⁻¹.

For stability analysis, carotenoid extract and Car-PNP-1s and extract were stored in amber-coloured vials at 5 °C for 5 weeks. Each sample was extracted and analysed using HPLC weekly using methods detailed earlier.

Results

Characterisation

Carotenoids are susceptible to oxidation; therefore, it is important to ensure that they are not decomposed during the formulation process. Table 2 shows the recovery of carotenoids from freshly prepared formulations as estimated using HPLC.

The processing temperatures of 60 and 40 °C were selected as these were 5 °C above pluronic F-68's melting temperature at atmospheric pressure and in scCO₂ at 100 bar, respectively. The results point to the possible detrimental effect of the processing temperature on carotenoid stability. In general, formulations prepared in scCO₂ had significantly higher carotenoid content than the ones processed at atmospheric pressure at 60 °C. The TIPT was

also performed at 120 °C (Car-PNP-0a), as suggested by Sang *et al* to compare the feasibility of Car-PNP formation according to their method [40]. Although it was possible to prepare nanoparticulate as seen from the DLS data but increase in temperature resulted in significantly higher degradation (> 50% loss of total carotenoids) of carotenoids. The major cause of carotenoid decomposition during processing and storage is widely accepted to be due to oxidation which is known to increase with higher processing temperature and longer processing times [43–45]. The processing time was kept constant in the preparation of nanoencapsulates in this work so it could be suggested that temperature played an important role in the reduction of carotenoid content in the formulation listed in Table 2. A comparison of Car-PNP-1a to Car-PNP-1s and the samples processed at 60 (Car-PNP-1a) and 120 °C (Car-PNP-0a) allude to the impact of processing temperature on the stability of carotenoids. Although further experiments may be needed to confirm this hypothesis, but these results suggest that the processing temperature accompanied by the absence of oxygen during scCO₂ processing may have had a positive impact in reducing carotenoid decomposition due to oxidation. Interestingly, Car-PNPs prepared at 40 °C and 10 MPa resulted in lower recovery of carotenoids than Car-PNP-1s but higher than Car-PNP-1a. This could be attributed to the partial phase transition/encapsulation at 40 °C down to the differences in density and mole content of CO₂ in the vessel along with the melt viscosity of the polymer that could provide better mixing at 60 °C than at 40 °C.

The scCO₂-extracted oil was composed of 47%, 35%, 17%, 0.1% and 0.1% of all-trans β-carotene, 9'-cis-β-carotene, all-trans-α-carotene, lutein and zeaxanthin, respectively. The HPLC analysis was performed for Car-PNPs and carotenoid extracts and the ratios (Table 3) of individual carotenoids in each formulation were calculated by normalising the concentration of all identified carotenoids with the concentration of 9'-cis β-carotene in the extract. Table 3 confirmed that the ratio of individual carotenoids recovered from each

formulation remained relatively the same as in the carotenoid extract regardless of formulation condition and carotenoid recovery percentage after formulation.

Based on these results, processing parameters of 60 °C and 10 MPa were chosen to prepare further formulations via TIPT. Car-PNPs were formulated with 5,10 and 20% of the carotenoid extract and particle size results are presented in Table 4.

All formulated Car-PNPs had a monomodal distribution with the particle sizes at different weight ratios of carotenoid extract varying within the range of ~150-250 nm. The average particle size increased with the extract content in the formulation. Similarly, PDI values for 10 and 20% formulations increased to ~0.5 from 0.3 (5% Car-PNP) indicating a broadening of particle size distribution with the increase in carotenoid content in the formulation [46].

SEM analysis showed the formation of spheroidal particles along with irregularly shaped structures as presented in Figure 4. Although a few discrete spherical or spheroidal structures could be seen at the higher magnification, but particles also appeared to be agglomerated or merged which could have occurred during the drying of the suspension before SEM analysis.

Figure 4. SEM micrographs of 5% carotenoid-loaded Pluronic nanoparticles. (Micrograph of nanoparticles at 5k magnification (left) and 90k magnification (right)).

The work reported by *Oh et al* presented cryo-TEM micrographs of nanoparticles that were comprised of a dark core consisting of paclitaxel-loaded PEG surrounded by a much lighter Pluronic F-68 outer shell, suggesting the formation of a core/shell structure [40]. Although, it is difficult to delineate this from the SEM micrographs shown in Figure 3, but a comparable morphology could be expected for these nanoparticulates where the extract dissolved in PEG could be assumed to be enveloped by pluronic F-68. The particle sizes obtained by SEM micrographs also complimented the values obtained using dynamic light scattering.

Solubility of carotenoids

The carotenoid solubility from each freshly prepared formulation was determined in deionised water and the results are presented in Table 5. A physical mixture of the polymers and crude carotenoid extract was also included in the study as controls. The recovery of carotenoids from each sample was obtained using HPLC and benchmarked against the carotenoids recovered in an ethanolic solution of the crude extract.

An improvement in the aqueous solubility of all carotenoids was seen when incorporated in Car-PNP formulations compared to the crude extract and physical mixture as shown in Table 5. The analysis of the recovery of individual carotenoids indicated the variability in the solubility of various carotenoids. For example, all-trans β -carotene was consistently the carotenoid with the least recovery in all Car-PNP formulations except for the Car-PNP-0a, and amongst xanthophylls, the aqueous solubility of lutein from Car-PNP formulations was higher than zeaxanthin regardless of the formulation. The effect of the processing method was also clear where the Car-PNP-1s formulation prepared in scCO₂ resulted in the highest (\approx 650-fold) total carotenoid content in water than any other. The recovery of total identified carotenoids in each formulation can be summarised as Car-PNP-1s > Car-PNP-2s > Car-PNP-0a > Car-PNP-1s* > Car-PNP-1a.

Stability of carotenoid-loaded polymer nanoparticles

The recoveries of 9'-cis β -carotene, all-trans β -carotene, all-trans α -carotene, lutein, and zeaxanthin in Car-PNP-1s and carotenoid extract during 5-week storage in the dark at 5 °C are presented in Figure 5 (A-E). The carotenes were generally more stable in the formulation than in the pure extract for the duration of the study while, for lutein and zeaxanthin, improved stability was observed only in the first 2 weeks of storage.

Figure 5. Stability of carotenoids in Car-PNP-1s and crude extract during 5-week storage.

The estimated degradation rates for carotenoids in Car-PNP-1s and the carotenoid extract was obtained from the regression equations and the degradation rate constants are presented in Table 6.

The stability of individual carotenoids can be summarised as follows; *all trans- α -carotene* > lutein > *all trans- β -carotene* > zeaxanthin > 9'-*cis* β -carotene in the crude extract and *all trans- α -carotene* > *all trans- β -carotene* > 9'-*cis* β -carotene > lutein > zeaxanthin in Car-PNP-1s. Although individual carotenoids exhibited degradation rate variability, the stability of carotenoids was higher in Car-PNP-1s suggesting that the stability of carotenoids is improved after nano-encapsulation.

Discussion

The bioavailability of carotenoids is limited owing to their poor aqueous solubility. Thus, carotenoid-containing food, formulations, and supplements typically require dispersion, emulsification, or encapsulation to modify solubility [10]. The adaptation of the method reported by Sang *et al* to the findings of Bhomia *et al* allowed the preparation of formulations under pressurised CO₂ at 60°C with minimal carotenoid oxidation which was significantly lower than the temperature previously used (120 °C) [24,40].

The self-assembly of amphiphilic polymers such as poloxamers caused by temperature changes is a comparatively easy way to obtain nanoparticles but it generally requires high temperatures. The dehydration of PPO chains upon melting causes them to interact with the carotenoid solution in PEG resulting in a core/shell structure as reported by Oh *et al* [40]. There have been previous attempts to reduce the high TIPT temperature e.g., Lee *et al* successfully prepared Pluronic based nanoparticles loaded with either caffeine, ibuprofen, or orlistat at 75 °C under atmospheric pressure and Yuk *et al* formulated docetaxel encapsulates

at 60 °C by changing the solubiliser from PEG to soybean oil/tween 80 mixture [47,48]. However, these modifications still remain insufficient for carotenoid processing because the stability of carotenoids is not only influenced by high temperatures, but oxidation is also a major concern [11]. El-Tinay and Chichester observed that β -carotene solubilised in toluene and treated at 60 °C with a stream of oxygen was oxidised, producing various epoxides [49]. In the present study, carotenoid decomposition was evident in the samples (Car-PNP-1a) formulated at 60 °C, under atmospheric pressure. However, TIPT (Car-PNP-1s) at 60°C in scCO₂, produced carotenoid nanoparticles that resulted in the minimal carotenoid loss. It was assumed that the carotenoid stability was maintained in scCO₂ due to the exclusion of atmospheric oxygen leading to the reduced decomposition by oxidation.

Microscopic imaging of Car-PNPs confirmed the formulation contained nano-sized particles. The average size of nanoparticles for each formulation was <250 nm with PDI <0.5. Oh, *et al.* also reported smaller particle sizes for corresponding sample loading [40]. Other studies have reported different particle size ranges (e.g., 144 - 249 nm) for β -carotene-loaded nanostructured lipid carriers [15]. Particle size variability can occur due to the size/volume of the encapsulant, quantity of payload, formulation method, excipients used and other complexities of the compound. The carotenoid extract used in the present study is a complex crude concentrate containing carotenoids and other lipids which may explain larger particle sizes when compared to previously reported studies. Results also showed that particle size was proportional to the percentage content of the carotenoid extract in the formulation. This is expected as a high loading will require a larger encapsulation surface. For example, Govender *et al.* prepared PLGA nanoparticles by nanoprecipitation and found that the particle size increased with increasing drug concentration [50]. Although, particle size changed with the carotene extract loading, but small PDI (<0.5) as obtained via dynamic light scattering measurements indicated a monomodal and comparatively narrow size distribution

of nanoparticles. In general, PDI values higher than 0.5 are indicative of broad distribution [12].

Improved aqueous solubility of carotenoid from polymeric nanoparticles formulated via TIPT was also seen as presented in Table 5. Surfactants or surfactant-like molecules are known to significantly improve the solubilisation of hydrophobic compounds as observed in this study [3]. The solubility of natural high-value carotenoids extracted from *Dunaliella* increased by 650-fold (total carotenoid) after nano-encapsulation in PEG and Pluronic, but the sheer presence of these polymers was not sufficient to obtain the solubility improvement as was seen from the results obtained for the physical mixture. Therefore, nano-encapsulation of carotenoids by TIPT was important to obtain both highly soluble and comparatively stable carotenoid formulations. The formulation method, processing parameters, and polymer composition had a clear influence on the solubility of the carotenoids. The aqueous solubility of carotenoids from the formulation containing PEG and prepared in scCO₂ (Car-PNP-2s and Car-PNP-1s) was significantly higher than Car-PNP-1s* (without PEG) which implies that PEG was important to obtain nanoencapsulates with the improved solubility of carotenoids. Also, phase transition temperature close to the melting point of Pluronic F-68 appeared to be insufficient to allow the required homogeneity of the mixture within the heating period used in this study. For example, the improvement in the aqueous solubility of carotenoids was obtained for the formulation prepared at 120 °C/0.1 MPa (Car-PNP-0a) than 60 °C/0.1 MPa (Car-PNP-1a). A similar effect was seen with the samples prepared at 40 °C and 60 °C in scCO₂ where the latter formulation resulted in the highest recovery of carotenoids. In some cases, it may be possible to resolve this issue by extending the processing time at lower temperatures [47]. However, processing for longer at any given temperature under atmospheric pressure may still result in higher degradation of thermosensitive and oxidation-prone molecules. Hence, it is compelling to develop formulation strategies that limit thermal

and oxidative degradation, such as via processing in scCO₂ as described in the current study. The melting point depression of Pluronics caused by the dissolution of CO₂ in the polymeric matrix allowed a considerable reduction in the processing temperature to perform TIPT at 60 °C (Car-PNP-1s) and also provided oxygen and solvent-free environment to reduce the decomposition of carotenoids during processing.

These types of strategies can have a significant impact on the development of formulations with improved shelf-life and the safe delivery of carotenoids or similar compounds. For example, the UK general population reportedly consumes, on average, ~3.1 mg of carotenoids daily [51]. 6–15 mg day⁻¹ of β-carotene is used for prophylactic treatment of conditions like psoriasis, vitiligo, and hairy leucoplakia and a dose of 150–180 mg day⁻¹ is used in the treatment of erythropoietic protoporphyria [51]. With increased aqueous solubility, carotenoid dose reduction may be attainable. For instance, 20 mg and 26 mg of the crude carotenoid extract would be required to attain 1 mg of 9'-cis β-carotene and all-trans β-carotene in solution. Whereas only 1.7 mg and 3.7 mg of Car-PNP-1s will be potentially required to achieve 1 mg of 9'-cis β-carotene and all-trans β-carotene based on the solubility data presented in Table 5.

The stability study showed that the stability of carotenoids is improved in Car-PNP-1s, although xanthophylls appeared to be more stable in the carotenoid extract than in Car-PNP-1s over the 5-week period. In Car-PNP-1s, lutein appeared to degrade quicker than carotenes whereas, in the carotenoid extract, lutein was the second most stable carotenoid. The poor stability of lutein identified in Car-PNP-1s conflicts with previous stability studies that found that lutein is more stable than β-carotene isomers [52,53]. Therefore, this suggests that the degradation observed in Car-PNP-1s is not solely due to the inherent oxidative vulnerability of carotenoids. It is also possible that the site of loading of carotenoids may have influenced the stability of the carotenoids. For example, it could be possible that carotenes were

deposited deep within the core while the xanthophylls are situated closer to the surface owing to the difference in their polarity. Consequently, it is possible that the xanthophylls (lutein and zeaxanthin) were more exposed and available for oxidation than carotenes. The solubility of carotenoids in scCO₂ is pressure dependent and usually increases with the increase in pressure at isothermal conditions. However, a review published by *Shi et al* suggests that considerably higher pressures are required to obtain carotenoid solubilities of any significance in scCO₂ [54]. This may indicate that the difference in the interaction of various components with the polymer could be negligible due to solubilisation and fractionation in the scCO₂ at 10 MPa. Nevertheless, the extract was presented as a solution in PEG so that could also impact how individual components may interact with the polymer and influence their encapsulation and stability in the studied system. Although Car-PNP1s improved the stability of some components of the extract, but these results are difficult to explain and certainly require further investigation.

Conclusion

Nanoencapsulation of natural high-value carotenoid extracts obtained from *Dunaliella* significantly improved the aqueous solubility of carotenoids. This study indicated that a temperature of 60 °C in scCO₂ (10 MPa) for Pluronic F-68 was sufficient to perform TIPT for the nanoencapsulation of carotenoids with minimal carotenoid decomposition. Following encapsulation, a 650-fold improvement of carotenoid aqueous solubility was recorded. Encapsulates containing carotenoids also showed improved stability, particularly of carotenes when stored at 5 °C. Conclusively, this study provides a novel solvent-free method to obtain formulations with improved aqueous solubility and shelf-life of carotenoids. However, further studies including encapsulation efficiency, release pattern and *in-vivo* bioavailability are required to establish the bio-accessibility of carotenoids from prepared polymeric nanoparticles.

Author contributions

Conceptualization: VT, PJH; methodology: VT, PJH; formal analysis: VT, CIW; investigation: VT, CIW; resources: VT, PJH; writing—original draft preparation: CIW, VT; writing—review and editing: CIW, VT, PJH; supervision: VT, PJH; project administration: VT, PJH; All authors have read and agreed to the published version of the manuscript.

Funding

This work received no external funding.

Conflict of interest

The authors report no declarations of interest.

Data availability

The data underlying this article will be shared on reasonable request to the corresponding author.

Accepted Manuscript

References

- [1] E. Nazemiyeh, M. Eskandani, H. Sheikhloie, H. Nazemiyeh, Formulation and physicochemical characterization of lycopene-loaded solid lipid nanoparticles, *Adv Pharm Bull.* 6 (2016). <https://doi.org/10.15171/apb.2016.032>.
- [2] L. Bogacz-Radomska, J. Harasym, β -Carotene-properties and production methods, *Food Quality and Safety.* 2 (2018). <https://doi.org/10.1093/fqsafe/fyy004>.
- [3] M.T. Kabir, M.H. Rahman, M. Shah, M.R. Jamiruddin, D. Basak, A. Al-Harrasi, S. Bhatia, G.M. Ashraf, A. Najda, A.F. El-kott, H.R.H. Mohamed, H.S. Al-malky, M.O. Germoush, A.E. Altyar, E.B. Alwafai, N. Ghaboura, M.M. Abdel-Daim, Therapeutic promise of carotenoids as antioxidants and anti-inflammatory agents in neurodegenerative disorders, *Biomedicine & Pharmacotherapy.* 146 (2022) 112610. <https://doi.org/10.1016/J.BIOPHA.2021.112610>.
- [4] M. Sun, F. Temelli, Supercritical carbon dioxide extraction of carotenoids from carrot using canola oil as a continuous co-solvent, *Journal of Supercritical Fluids.* 37 (2006). <https://doi.org/10.1016/j.supflu.2006.01.008>.
- [5] D.B.R. Amaya, *Food Carotenoids: Chemistry, Biology and Technology*, 2015. <https://doi.org/10.1002/9781118864364>.
- [6] M. de Andrade Lima, I. Kestekoglou, D. Charalampopoulos, A. Chatzifragkou, Supercritical fluid extraction of carotenoids from vegetable waste matrices, *Molecules.* 24 (2019). <https://doi.org/10.3390/molecules24030466>.
- [7] I.E. Apanasenko, O. Yu, N.E. Polyakov, L.P. Suntsova, E.S. Meteleva, A. V Dushkin, P. Vachali, P.S. Bernstein, Solubilization and stabilization of macular carotenoids by water soluble oligosaccharides and polysaccharides, *Arch Biochem Biophys.* 572 (2015) 58–65. <https://doi.org/10.1016/j.abb.2014.12.010>.
- [8] J. Yi, T.I. Lam, W. Yokoyama, L.W. Cheng, F. Zhong, Food Hydrocolloids Beta-carotene encapsulated in food protein nanoparticles reduces peroxy radical oxidation in Caco-2 cells, *Food Hydrocoll.* 43 (2015) 31–40. <https://doi.org/10.1016/j.foodhyd.2014.04.028>.
- [9] D.T. Santos, Á. Martín, M.A.A. Meireles, M.J. Cocero, Production of stabilized sub-micrometric particles of carotenoids using supercritical fluid extraction of emulsions, *Journal of Supercritical Fluids.* 61 (2012). <https://doi.org/10.1016/j.supflu.2011.09.011>.
- [10] E. Fernández-García, I. Carvajal-Lérida, M. Jarén-Galán, J. Garrido-Fernández, A. Pérez-Gálvez, D. Hornero-Méndez, Carotenoids bioavailability from foods: From plant pigments to efficient biological activities, *Food Research International.* 46 (2012). <https://doi.org/10.1016/j.foodres.2011.06.007>.
- [11] C.S. Boon, D.J. McClements, J. Weiss, E.A. Decker, Factors influencing the chemical stability of carotenoids in foods, *Crit Rev Food Sci Nutr.* 50 (2010). <https://doi.org/10.1080/10408390802565889>.

- [12] P.P. dos Santos, L. de A. Andrade, S.H. Flôres, A. de O. Rios, Nanoencapsulation of carotenoids: a focus on different delivery systems and evaluation parameters, *J Food Sci Technol.* 55 (2018) 3851–3860. <https://doi.org/10.1007/s13197-018-3316-6>.
- [13] A. Akhoond Zardini, M. Mohebbi, R. Farhoosh, S. Bolurian, Production and characterization of nanostructured lipid carriers and solid lipid nanoparticles containing lycopene for food fortification, *J Food Sci Technol.* 55 (2018). <https://doi.org/10.1007/s13197-017-2937-5>.
- [14] C. Yang, H. Yan, X. Jiang, H. Xu, R. Tsao, L. Zhang, Preparation of 9 Z- β -Carotene and 9 Z- β -Carotene High-Loaded Nanostructured Lipid Carriers: Characterization and Storage Stability, *J Agric Food Chem.* 68 (2020). <https://doi.org/10.1021/acs.jafc.0c02342>.
- [15] A. Hentschel, S. Gramdorf, R.H. Müller, T. Kurz, β -Carotene-loaded nanostructured lipid carriers, *J Food Sci.* 73 (2008). <https://doi.org/10.1111/j.1750-3841.2007.00641.x>.
- [16] E. Kotake-Nara, A. Nagao, Effects of mixed micellar lipids on carotenoid uptake by human intestinal Caco-2 cells, *Biosci Biotechnol Biochem.* 76 (2012). <https://doi.org/10.1271/bbb.110777>.
- [17] S. Singh, V.K. Pandey, R.P. Tewari, V. Agarwal, Nanoparticle based drug delivery system: Advantages and applications, *Indian J Sci Technol.* 4 (2011). <https://doi.org/10.17485/ijst/2011/v4i3/29960>.
- [18] A. Martín, F. Mattea, L. Gutiérrez, F. Miguel, M.J. Cocero, Co-precipitation of carotenoids and bio-polymers with the supercritical anti-solvent process, *Journal of Supercritical Fluids.* 41 (2007). <https://doi.org/10.1016/j.supflu.2006.08.009>.
- [19] E. Reverchon, A. Antonacci, Polymer microparticles production by supercritical assisted atomization, *Journal of Supercritical Fluids.* 39 (2007). <https://doi.org/10.1016/j.supflu.2006.03.005>.
- [20] E. Reverchon, G. Lamberti, A. Antonacci, Supercritical fluid assisted production of HPMC composite microparticles, *Journal of Supercritical Fluids.* 46 (2008). <https://doi.org/10.1016/j.supflu.2008.04.010>.
- [21] M. Bahrami, S. Ranjbarian, Production of micro- and nano-composite particles by supercritical carbon dioxide, *Journal of Supercritical Fluids.* 40 (2007). <https://doi.org/10.1016/j.supflu.2006.05.006>.
- [22] A.A. D'souza, R. Shegokar, Polyethylene glycol (PEG): a versatile polymer for pharmaceutical applications, *Expert Opin Drug Deliv.* 13 (2016). <https://doi.org/10.1080/17425247.2016.1182485>.
- [23] V.A. Feitosa, V.C. de Almeida, B. Malheiros, R.D. de Castro, L.R.S. Barbosa, N.N.P. Cerize, C. de O. Rangel-Yagui, Polymeric micelles of pluronic F127 reduce hemolytic potential of amphiphilic drugs, *Colloids Surf B Biointerfaces.* 180 (2019). <https://doi.org/10.1016/j.colsurfb.2019.04.045>.

- [24] R. Bhomia, V. Trivedi, J.C. Mitchell, N.J. Coleman, M.J. Snowden, Effect of Pressure on the Melting Point of Pluronics in Pressurized Carbon Dioxide, *Ind Eng Chem Res.* 53 (2014) 10820–10825. <https://doi.org/10.1021/ie501344m>.
- [25] M. Yang, S.K. Lai, Y.Y. Wang, W. Zhong, C. Happe, M. Zhang, J. Fu, J. Hanes, Biodegradable nanoparticles composed entirely of safe materials that rapidly penetrate human mucus, *Angewandte Chemie - International Edition.* 50 (2011). <https://doi.org/10.1002/anie.201006849>.
- [26] D. Dantas Lopes dos Santos, J.F. Besegato, P.B.G. de Melo, J.A. Oshiro Junior, M. Chorilli, D. Deng, V.S. Bagnato, A.N. de S. Rastelli, Curcumin-loaded Pluronic® F-127 Micelles as a Drug Delivery System for Curcumin-mediated Photodynamic Therapy for Oral Application, *Photochem Photobiol.* 97 (2021). <https://doi.org/10.1111/php.13433>.
- [27] J. Cacaccio, F. Durrani, R.R. Cheruku, B. Borah, M. Ethirajan, W. Tabaczynski, P. Pera, J.R. Missert, R.K. Pandey, Pluronic F-127: An Efficient Delivery Vehicle for 3-(1'-hexyloxy)ethyl-3-devinylpyropheophorbide-a (HPPH or Photochlor), *Photochem Photobiol.* 96 (2020). <https://doi.org/10.1111/php.13183>.
- [28] A.M. Bodratti, P. Alexandridis, Functional Biomaterials Formulation of Poloxamers for Drug Delivery, *J Funct Biomater.* 9 (2018).
- [29] A. Kumari, S.K. Yadav, S.C. Yadav, Biodegradable polymeric nanoparticles based drug delivery systems, *Colloids Surf B Biointerfaces.* 75 (2010). <https://doi.org/10.1016/j.colsurfb.2009.09.001>.
- [30] H. Wei, R.X. Zhuo, X.Z. Zhang, Design and development of polymeric micelles with cleavable links for intracellular drug delivery, *Prog Polym Sci.* 38 (2013). <https://doi.org/10.1016/j.progpolymsci.2012.07.002>.
- [31] A.L. Ajiboye, V. Trivedi, J.C. Mitchell, Preparation of polycaprolactone nanoparticles via supercritical carbon dioxide extraction of emulsions, *Drug Deliv Transl Res.* 8 (2018). <https://doi.org/10.1007/s13346-017-0422-3>.
- [32] R. Campardelli, G. della Porta, E. Reverchon, Solvent elimination from polymer nanoparticle suspensions by continuous supercritical extraction, *Journal of Supercritical Fluids.* 70 (2012). <https://doi.org/10.1016/j.supflu.2012.06.005>.
- [33] G. della Porta, R. Campardelli, E. Reverchon, Monodisperse biopolymer nanoparticles by Continuous Supercritical Emulsion Extraction, *Journal of Supercritical Fluids.* 76 (2013). <https://doi.org/10.1016/j.supflu.2013.01.009>.
- [34] L. Martin, S. Liparoti, G. della Porta, R. Adami, J.L. Marqués, J.S. Urieta, A.M. Mainar, E. Reverchon, Rotenone coprecipitation with biodegradable polymers by supercritical assisted atomization, *Journal of Supercritical Fluids.* 81 (2013). <https://doi.org/10.1016/j.supflu.2013.03.032>.

- [35] G. della Porta, N. Falco, E. Giordano, E. Reverchon, PLGA microspheres by Supercritical Emulsion Extraction: A study on insulin release in myoblast culture, *J Biomater Sci Polym Ed.* 24 (2013). <https://doi.org/10.1080/09205063.2013.807457>.
- [36] R. Campardelli, E. Oleandro, M. Scognamiglio, G. della Porta, E. Reverchon, Palmitoylethanolamide sub-micronization using fast precipitation followed by supercritical fluids extraction, *Powder Technol.* 305 (2017). <https://doi.org/10.1016/j.powtec.2016.09.084>.
- [37] I. Palazzo, M. Raimondo, G. della Porta, L. Guadagno, E. Reverchon, Encapsulation of health-monitoring agent in poly-methyl-methacrylate microcapsules using supercritical emulsion extraction, *Journal of Industrial and Engineering Chemistry.* 90 (2020). <https://doi.org/10.1016/j.jiec.2020.07.026>.
- [38] C. Gimenez-Rota, I. Palazzo, M.R. Scognamiglio, A. Mainar, E. Reverchon, G. della Porta, B-Carotene, A-tocopherol and rosmarinic acid encapsulated within PLA/PLGA microcarriers by supercritical emulsion extraction: Encapsulation efficiency, drugs shelf-life and antioxidant activity, *Journal of Supercritical Fluids.* 146 (2019). <https://doi.org/10.1016/j.supflu.2019.01.019>.
- [39] D.F. Tirado, I. Palazzo, M. Scognamiglio, L. Calvo, G. della Porta, E. Reverchon, Astaxanthin encapsulation in ethyl cellulose carriers by continuous supercritical emulsions extraction: A study on particle size, encapsulation efficiency, release profile and antioxidant activity, *Journal of Supercritical Fluids.* 150 (2019). <https://doi.org/10.1016/j.supflu.2019.04.017>.
- [40] K.S. Oh, J.Y. Song, S.H. Cho, B.S. Lee, S.Y. Kim, K. Kim, H. Jeon, I.C. Kwon, S.H. Yuk, Paclitaxel-loaded Pluronic nanoparticles formed by a temperature-induced phase transition for cancer therapy, *Journal of Controlled Release.* 148 (2010). <https://doi.org/10.1016/j.jconrel.2010.08.021>.
- [41] M. Syamila, M.A. Gedi, R. Briars, C. Ayed, D.A. Gray, Effect of temperature, oxygen and light on the degradation of β -carotene, lutein and α -tocopherol in spray-dried spinach juice powder during storage, *Food Chem.* 284 (2019). <https://doi.org/10.1016/j.foodchem.2019.01.055>.
- [42] A.V.M. Nunes, C.M.M. Duarte, Dense CO₂ as a Solute, Co-Solute or Co-Solvent in Particle Formation Processes: A review, *Materials.* 4 (2011). <https://doi.org/10.3390/ma4112017>.
- [43] S.S. Kadian, A. Sharma, D.R. Sood, Effect of Light and Heat on Stability of Crude Carotenoid Extract From Natural Sources, *Int J Pharm Sci Res.* 4 (2013).
- [44] N. Thakur, Heat stability and antioxidant potential of beta-carotene isolated from a fungal isolate, *Bulgarian Journal of Agricultural Science.* 24 (2018).
- [45] E. Demiray, Y. Tulek, Degradation kinetics of β -carotene in carrot slices during convective drying, *Int J Food Prop.* 20 (2017). <https://doi.org/10.1080/10942912.2016.1147460>.

- [46] P. Mukhopadhyay, P.P. Kundu, Chitosan-graft-PAMAM-alginate core-shell nanoparticles: a safe and promising oral insulin carrier in an animal model, *RSC Adv.* 5 (2015). <https://doi.org/10.1039/c5ra17729d>.
- [47] H. Lee, J.Y. Kim, E.J. Koo, J. Lee, E.H. Lee, K.S. Oh, S.H. Yuk, Nanoencapsulation of drug-loaded lipid by temperature-induced phase transition, *Chem Biochem Eng Q.* 26 (2012).
- [48] S.H. Yuk, K.S. Oh, J. Park, E.H. Lee, K. Kim, I.C. Kwon, Docetaxel-loaded composite nanoparticles formed by a temperature-induced phase transition for cancer therapy, *J Bioact Compat Polym.* 27 (2012). <https://doi.org/10.1177/0883911512448752>.
- [49] A.H. El-Tinay, C.O. Chichester, Oxidation of β -Carotene. Site of Initial Attack, *Journal of Organic Chemistry.* 35 (1970). <https://doi.org/10.1021/jo00832a040>.
- [50] T. Govender, S. Stolnik, M.C. Garnett, L. Illum, S.S. Davis, PLGA nanoparticles prepared by nanoprecipitation: Drug loading and release studies of a water soluble drug, *Journal of Controlled Release.* 57 (1999). [https://doi.org/10.1016/S0168-3659\(98\)00116-3](https://doi.org/10.1016/S0168-3659(98)00116-3).
- [51] M. Jenab, S. Salvini, C.H. van Gils, M. Brustad, S. Shakya-Shrestha, B. Buijsse, H. Verhagen, M. Touvier, C. Biessy, P. Wallström, K. Bouckaert, E. Lund, M. Waaseth, N. Roswall, A.M. Joensen, J. Linseisen, H. Boeing, E. Vasilopoulou, V. Dilis, S. Sieri, C. Sacerdote, P. Ferrari, J. Manjer, S. Nilsson, A.A. Welch, R. Travis, M.C. Boutron-Ruault, M. Niravong, H.B. Bueno-De-Mesquita, Y.T. van der Schouw, M.J. Tormo, A. Barricarte, E. Riboli, S. Bingham, N. Slimani, Dietary intakes of retinol, β -carotene, vitamin D and vitamin E in the european prospective investigation into cancer and nutrition cohort, *Eur J Clin Nutr.* 63 (2009). <https://doi.org/10.1038/ejcn.2009.79>.
- [52] Y. dong Xiao, W. yang Huang, D. jing Li, J. feng Song, C. quan Liu, Q. yu Wei, M. Zhang, Q. ming Yang, Thermal degradation kinetics of all-trans and cis-carotenoids in a light-induced model system, *Food Chem.* 239 (2018). <https://doi.org/10.1016/j.foodchem.2017.06.107>.
- [53] A. Zeb, Thermal degradation of β -carotene in food oils, *Food and Nutritional Components in Focus.* 1 (2012).
- [54] J. Shi, G. Mittal, E. Kim, S.J. Xue, Solubility of carotenoids in supercritical CO₂, *Food Reviews International.* 23 (2007). <https://doi.org/10.1080/87559120701593806>.

Figure 1. Generalised structure of a PEO-PPO-PEO triblock (A) polymer (x and y represent the length of PEO and PPO blocks, respectively) and polyethylene glycol (B).

Figure 2: Schematic presentation of SCF instrument [CO₂ cylinder (A), chiller (B), CO₂ pump (C), high pressure vessel (RV), automatic back pressure regulator (ABPR), temperature controller (D) and display unit (E)].

Figure 3: Schematic representation of the nanoparticulates' preparation process.

Figure 4. SEM micrographs of 5% carotenoid-loaded Pluronic nanoparticles. (Micrograph of nanoparticles at 5k magnification (left) and 90k magnification (right)).

Figure 5. Stability of carotenoids in Car-PNP-1s and crude extract during 5-week storage.

Accepted Manuscript

Table 1: Formulation descriptors.

Formulation	Pressure (MPa)	Temperature (°C)	Polymer/s
Car-PNP-0a	0.1	120	PEG/Pluronic F-68
Car-PNP-1a	0.1	60	PEG/Pluronic F-68
Car-PNP-1s	10	60	PEG/Pluronic F-68
Car-PNP-2s	10	40	PEG/Pluronic F-68
Car-PNP-1s*	10	60	Pluronic F-68

Each formulation code comprises of a generic indicator -Car-PNP, a temperature indicator (0,1 or 2) and a pressure indicator (a or s).

Accepted Manuscript

Table 2. The percentage (%) recovery of carotenoids in Car-PNP formulations

Carotenoids	Car-PNP- 0a	Car-PNP- 1a	Car-PNP- 1s	Car- PNP- 2s	Car- PNP- 1s*
9' -cis β-carotene	44.0 \pm 0.5	63.3 \pm 0.3	95.9 \pm 1.5	80.4 \pm 0.3	100.9 \pm 1.3
All-trans β-carotene	43.2 \pm 0.6	68.3 \pm 0.2	98.5 \pm 0.8	75.9 \pm 0.5	100.0 \pm 2.7
All-trans α-carotene	55.5 \pm 0.7	73.8 \pm 0.3	99.1 \pm 0.2	78.7 \pm 0.6	101.1 \pm 2.4
Lutein	29.2 \pm 0.2	67.6 \pm 0.8	92.2 \pm 1.5	85.0 \pm 1.4	89.3 \pm 2.7
Zeaxanthin	28.0 \pm 0.9	64.2 \pm 2.3	97.5 \pm 1.2	77.4 \pm 1.2	87.9 \pm 3.7
Total carotenoids	43.6 \pm 0.1	66.3 \pm 0.1	97.4 \pm 1.5	78.5 \pm 0.13	99.9 \pm 4.7

*†*The values shown are the percentage of the corresponding carotenoid in the carotenoid extract which was recovered in each sample of Car-PNP. Values are the mean of three replicates \pm SD.

Accepted Manuscript

Table 3. The ratio of individual carotenoids in each formulation normalised to 9'-cis β -carotene

	Retention time (min)	Car- PNP- 0a	Car- PNP- 1a	Car- PNP- 1s	Car- PNP- 2s	Car- PNP- 1s*	Crude Extract
9' -cis β -carotene	34.1 \pm 1.3	1.00	1.00	1.00	1.00	1.00	1.00
All-trans β -carotene	29.3 \pm 1.8	0.84	0.93	0.83	0.82	0.85	0.80
All-trans α -carotene	22.9 \pm 1.6	0.20	0.19	0.17	0.16	0.16	0.17
Lutein	6.8 \pm 0.4	0.03	0.05	0.05	0.05	0.04	0.05
Zeaxanthin	7.9 \pm 0.6	0.02	0.03	0.03	0.03	0.03	0.03

Accepted Manuscript

Table 4. The average particle size of carotenoid-loaded polymer nanoparticles

Car-PNP-1s	Average particle size (nm)	PDI
5 %	158 ±0.4	0.29 ±0.02
10 %	208 ±3	0.45 ±0.03
20 %	234 ±12.1	0.50 ±0.08

Accepted Manuscript

Table 5. The percentage (%) recovery of carotenoids in deionised water.

	Crude Extract	Physical mixture	Car- PNP-0a	Car- PNP- 1a	Car- PNP- 1s	Car- PNP- 2s	Car- PNP- 1s*
9' -cis β-carotene	0.08 \pm 0.01	1.2 \pm 0.2	28.5 \pm 0.8	19.5 \pm 1.5	57.0 \pm 2.8	53.3 \pm 4.8	30.9 \pm 1.1
All-trans β-carotene	0.5 \pm 0.01	0.8 \pm 0.1	20.7 \pm 2.3	14.0 \pm 1.5	27.1 \pm 1.0	23.4 \pm 1.3	13.1 \pm 0.5
All-trans α-carotene	0.1 \pm 0.02	2.0 \pm 0.4	28.3 \pm 1.8	23.6 \pm 3.0	71.7 \pm 0.8	37.6 \pm 4.4	23.0 \pm 1.4
Lutein	0.2 \pm 0.01	1.1 \pm 0.1	22.0 \pm 0.5	40.1 \pm 4.8	63.4 \pm 6.3	54.8 \pm 7.6	50.6 \pm 3.6
Zeaxanthin	0.4 \pm 0.03	8.4 \pm 0.3	16.2 \pm 3.1	31.0 \pm 3.6	51.2 \pm 3.1	35.5 \pm 4.3	36.0 \pm 4.1
Total carotenoids	0.07 \pm0.01	1.2 \pm0.2	25.4 \pm1.2	18.6 \pm1.3	45.7 \pm2.6	40.8 \pm3.7	23.9 \pm0.8


*†*Values are the percentage of corresponding carotenoids originally quantified in an ethanolic solution of the carotenoid extract that was recovered from an aqueous solution of each test sample. Values are mean \pm SD ($n=3$).

Table 6. Estimated rate constants (wk^{-1}) for first-order degradation of carotenoids in Car-PNP-1s and crude extract after 5-week storage in the dark at 5 °C.

Carotenoid	Car-PNP-1s	Crude Extract
9' -cis β-carotene	0.138	0.227
All-trans β-carotene	0.122	0.198
All-trans α-carotene	0.104	0.150
Lutein	0.211	0.176
Zeaxanthin	0.219	0.208
Total carotenoids	0.138	0.188


Accepted Manuscript

Figure 1




Accepted Manuscript

Figure 2

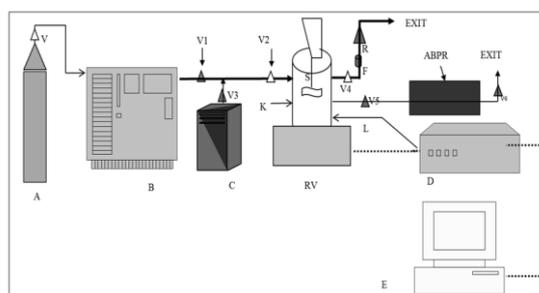


Accepted Manuscript

Figure 3

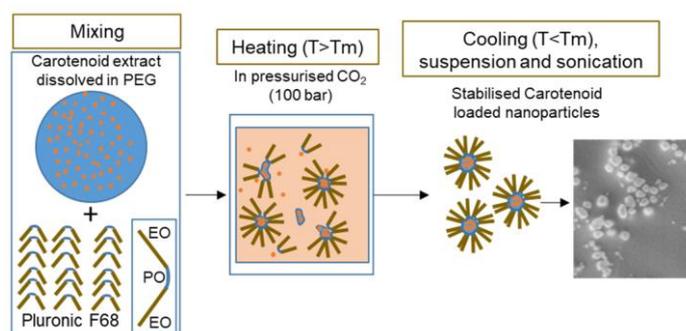


Accepted Manuscript

Figure 4

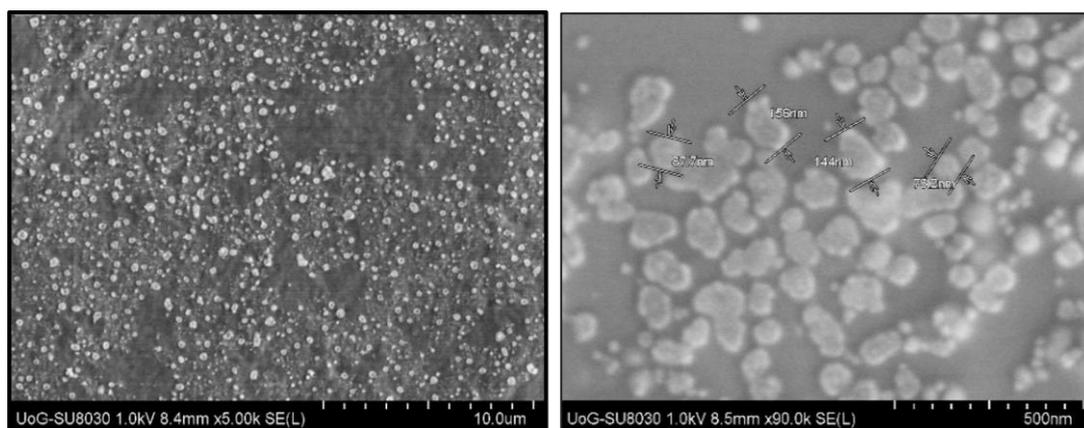

Accepted Manuscript

Figure 5

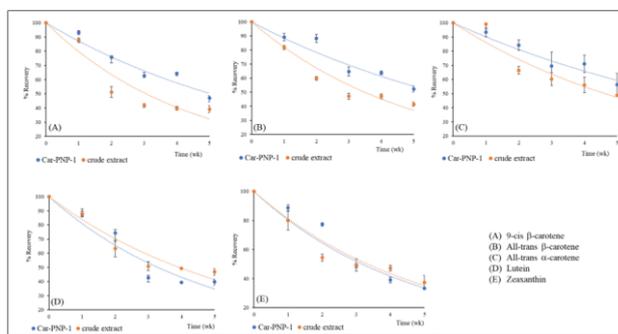

Accepted Manuscript